

Zeitschrift: IABSE congress report = Rapport du congrès AIPC = IVBH
Kongressbericht

Band: 8 (1968)

Artikel: Performance of steel beams and their connections to columns during
severe cyclic loading

Autor: Popov, E.P.

DOI: <https://doi.org/10.5169/seals-8806>

Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

Conditions d'utilisation

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

Download PDF: 02.07.2025

ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>

IIIc

Performance of Steel Beams and Their Connections to Columns During Severe Cyclic Loading

Comportement de poutres en acier et de leur assemblage sur colonnes sous d'importantes charges périodiques

Das Verhalten von Stahlträgern und ihren Anschlüssen an Stützen unter schweren zyklischen Belastungen

E.P. POPOV

Professor of Civil Engineering
University of California, Berkeley

Introduction

In the Preliminary Publication for the 1968 IABSE Eighth Congress, D. Sfintesco makes reference to some of the earlier work at the University of California on steel beam-to-column connections subjected to repeated and reversed loading (1, 2). It is the purpose of this discussion to call attention to further published results (3, 4) and to provide the readers with a summary on the new work which should shortly become generally available in print (5, 6). It is gratifying that the earlier analyses as well as the penetrating opinions and observations by D. Sfintesco expressed in the Preliminary Publication are in essential agreement with the later findings.

Conventional stationary structures such as buildings, bridges and towers are not immune to dynamic loadings. As pointed out by J. Ferry Borges in the Preliminary Publication, such loadings are associated with wind and earthquake, as well as machinery, traffic, and blast loads. The general effect on stationary structures due to such loads is essentially analogous. However, the loading of buildings caused by strong earthquakes is particularly severe.

During an earthquake the soil on which a building is situated becomes subjected to a rapid back-and-forth motion in horizontal and vertical directions. The horizontal motion usually causes the more damaging effect. A representative accelerogram for a horizontal movement for an earthquake (7) is shown in Fig. 1. The typical rapidly varying inputs at the ground level reflect themselves in relatively slow swaying motions of buildings. This is

due to the fortunate lack of resonance between the frequency of the ground motion input and the natural period of vibration of typical high-rise buildings.


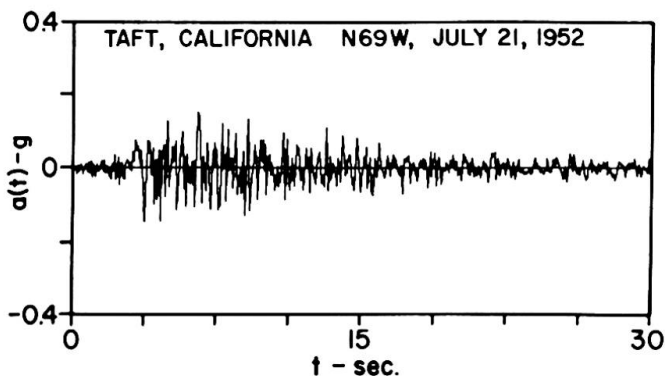


Fig. 1

The swaying motion of a severely strained building is shown schematically in Figs. 2(a) and (b), where it is assumed that the columns are relatively inflexible. This is in conformity with the current design practice which permits

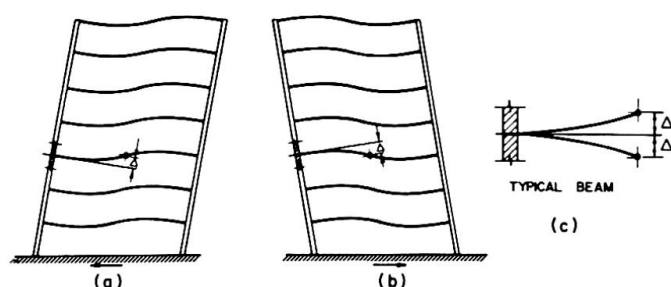

BEHAVIOR OF A FRAME IN AN EARTHQUAKE

Fig. 2

essentially only elastic action in the column, but allows substantial inelastic deformation in the beams and their connections to the columns.

On the above basis all specimens for the first series of the California experiments were so designed that yielding occurred in the beams and their connections and not in the columns. Such yielding of the members provides damping of the structure and assures dissipation of the energy input due to an external cause such as an earthquake.

In the specimens designed for this series of experiments no attempt was made to simulate gravity loading. The question of simulating more accurately the loading on actual beams, as well as of permitting columns to exhibit some controlled yielding, is the subject of a current investigation (8).

Details of Specimens

The specimens selected in the first series of the California tests resembled the isolated element of a building frame shown in Fig. 2(c). The details of the specimens are shown in Figs. 3, 4, 5, and 6. In the specimens of the F1 type,

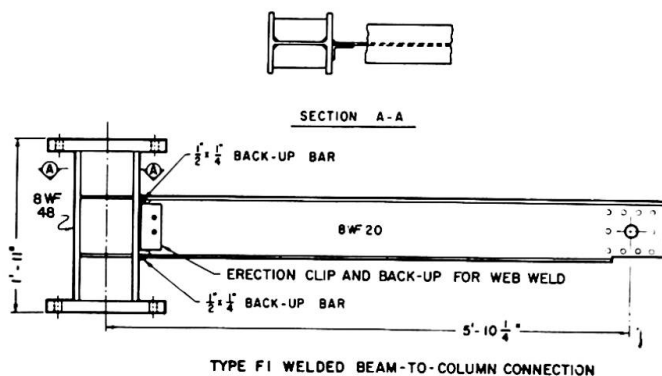


Fig. 3

Fig. 3, the beam was directly welded to the column stub. In the specimen of the F2 type, Fig. 4, welded connecting plates were used. In the specimen of the F3 type, Fig. 5, the attachment of the beam to the column stub through the connecting plates was achieved using high-strength bolts. The welded detail W1 for connecting a beam to the web of the column is shown in Fig. 6. All of these details represent the types widely used in the construction of steel buildings.

In several of the specimens of the F2 and the F3 types the thickness of the connecting plates was varied. For two web connected specimens, designated as W2, the connecting plates were tapered or shaped to provide a more gradual change in the cross-section of the beam flange. A total of twenty specimens using A-36 steel were fabricated according to above details. Four additional specimens, two of the F1 type and two of the F2 type, using A-441 steel formed a part of the same series of experiments (4, 5). The specimens made of a higher strength steel are identified by letters HS and referred to as F1HS and F2HS.

Experimental Procedure

The basic experimental set-up is shown in the photograph of Fig. 7. A double acting hydraulic cylinder provided the desired load input at the tip of the cantilever. Experiments were controlled either by a strain gage near the built-in end of the cantilever, or by a selected tip deflection. Some typical loading programs are shown in Fig. 8. A considerable variety of such programs was used in the experiments.

In Fig. 8(a) the step-ladder type of sequence for the tip deflection is shown. Here the displacement amplitudes are arbitrarily increased gradually. An experiment with a few strong initial displacements followed by the step-ladder sequence of the tip deflection is shown in Fig. 8(b).

Numerous measurements were recorded during the experiments (4, 5). Among these the load-deflection characteristics of the beam are particularly important.

Principal Experimental Results

Applying repeated and reversed loading of the type shown in Fig. 8 causes considerable yielding in the specimens during each cycle of loading application. Therefore, as is to be expected, after a number of cycles the specimens fail. The manner of failure is strongly dependent on the type of specimen, whereas the number of cycles to failure depends on the amplitudes of the tip deflection. These results are summarized in Table 1. For a more complete description of the experiments and the results, the reader is referred to References 4 and 5.

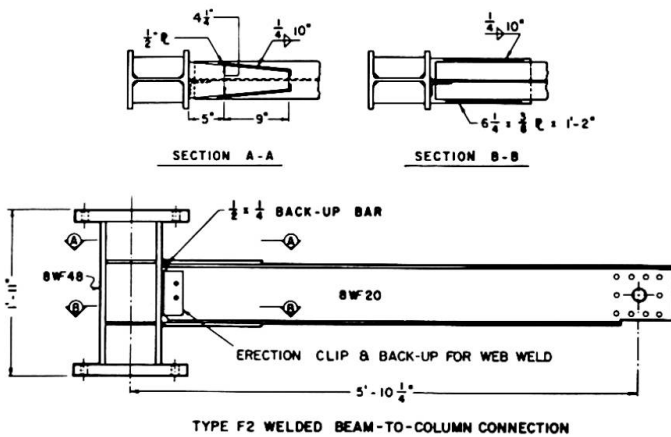


Fig. 4

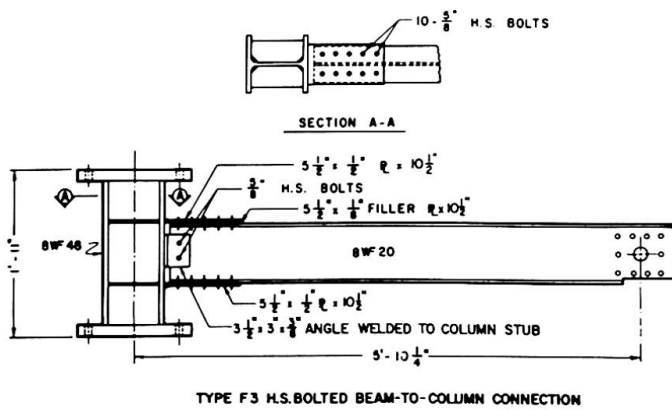


Fig. 5

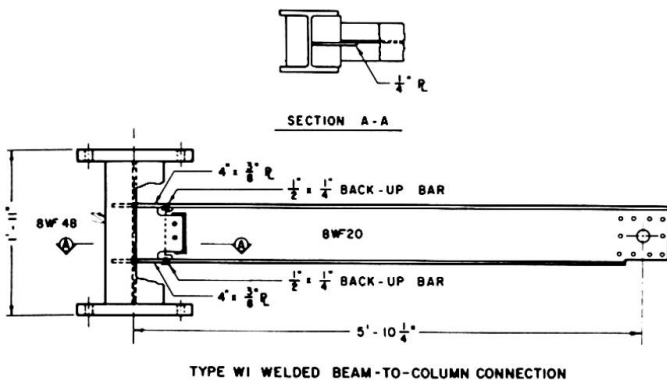


Fig. 6

TABLE I

Specimen	Cycles to Failure	Type of Cycling Number of Cycles at Given Tip Deflection *	Total Energy Absorption kip - in.
F1-C1	28	5 at ± 1 in.; 5 at ± 2 in.; 10 at ± 3 in.; 8 at ± 4 in.	-----
F1-C2	22 1/2	22 1/2 at ± 3 in.	2,411
F1-C3	120	100 at ± 1 in.; 20 at ± 3 in.	3,734
F1-C4	39 1/2	20 at ± 2 in.; 19 1/2 at ± 3 in.	2,837
F1-C6	32	5 at $\pm 3/4$ in.; 5 at $\pm 1 1/2$ in.; 10 at $\pm 1 1/2$ in. to ± 4 in.; 12 at ± 4 in.	2,574
F2-C1	18	5 at ± 1 in.; 5 at $\pm 1 1/2$ in.; 8 at ± 3 in.	-----
F2-C4	44	42 at $\pm 1 1/2$ in.; 2 at ± 2 in.	2,495
F2A-C7	38 1/2	15 at $\pm 3/4$ in.; 15 at $\pm 1 1/4$ in.; 8 1/2 at $\pm 1 3/4$ in.	1,054
F2B-C8	32 1/2	15 at $\pm 3/4$ in.; 15 at $\pm 1 1/4$ in.; 2 1/2 at $\pm 1 3/4$ in.	533
F3-C1	9 1/2	5 at $\pm 2 1/2$ in.; 4 1/2 at ± 4 in.	-----
F3-C5	30	30 at approximately $\pm 2 1/2$ in.	1,533
F3A-C7	65 1/2	15 at $\pm 3/4$ in.; 15 at $\pm 1 1/4$ in.; 15 at $\pm 1 3/4$ in.; 15 at $\pm 2 1/4$ in.; 5 1/2 at ± 3 in.	2,488
F3B-C7	33 1/2	15 at $\pm 3/4$ in.; 15 at $\pm 1 1/4$ in.; 3 1/2 at $\pm 1 3/4$ in.	704
W1-C7 **	37	15 at $\pm 3/4$ in.; 15 at $\pm 1 1/4$ in.; 7 at ± 2 in.	926
W1-C9	51 1/2	2 at $\pm 1 3/4$ in.; 15 at $\pm 3/4$ in.; 15 at $\pm 1 1/4$ in.; 15 at $\pm 1 3/4$ in.; 4 1/2 at $\pm 2 1/4$ in.	1,500
W2A-C7	46 1/2	15 at $\pm 3/4$ in.; 15 at $\pm 1 1/4$ in.; 15 at $\pm 1 3/4$ in.; 1 1/2 at $\pm 2 1/4$ in.	1,189
W2B-C10	30	5 at $\pm 1 3/4$ in.; 15 at $\pm 3/4$ in.; 10 at $\pm 1 1/4$ in.	651
FLHS-C7	74	15 at $\pm 3/4$ in.; 15 at $\pm 1 1/4$ in.; 15 at $\pm 1 3/4$ in.; 15 at $\pm 2 1/4$ in.; 14 at $\pm 2 3/4$ in.	3,597
FLHS-C11	73	5 at $\pm 2 1/4$ in.; 15 at $\pm 3/4$ in.; 15 at $\pm 1 1/4$ in.; 15 at $\pm 1 3/4$ in.; 15 at $\pm 2 1/4$ in.; 8 at $\pm 2 3/4$ in.	3,539
F2HS-C7	35 1/2	15 at $\pm 3/4$ in.; 15 at $\pm 1 1/4$ in.; 5 1/2 at $\pm 1 3/4$ in.	897
F2HS-C9	54 1/2	2 at $\pm 1 3/4$ in.; 15 at $\pm 3/4$ in.; 15 at $\pm 1 1/4$ in.; 15 at $\pm 1 3/4$ in.; 7 1/2 at $\pm 2 1/4$ in.	2,149

* Tip deflections are approximate, and are measured from mean position.

** Results from two defectively fabricated W1 specimens are not included.

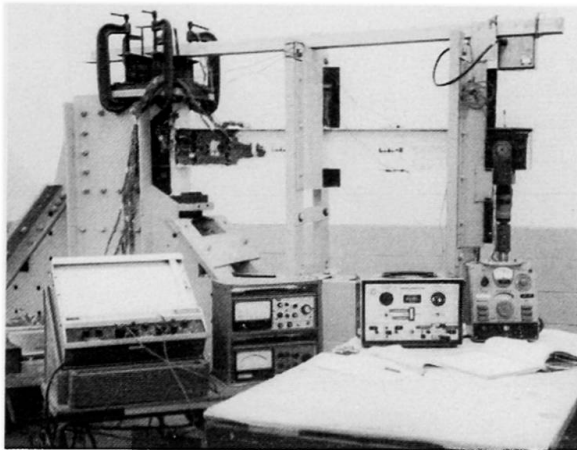


Fig. 7

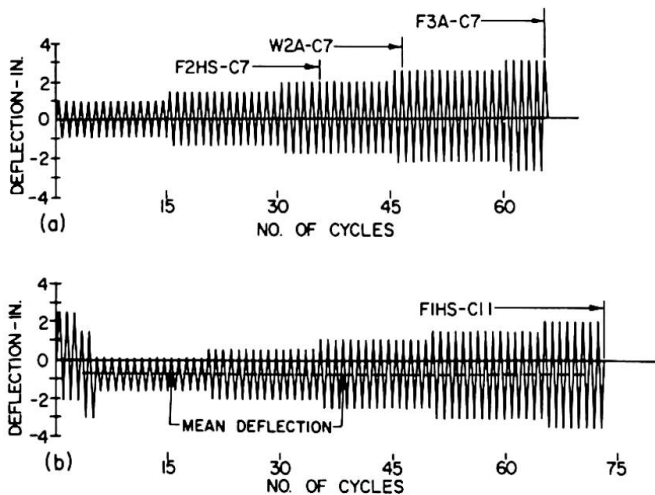


Fig. 8

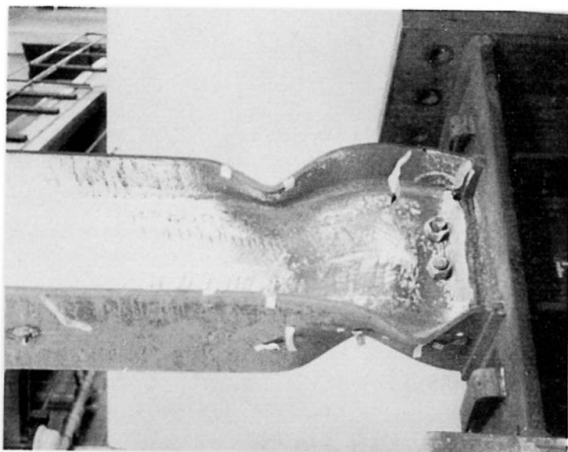


Fig. 9

A few photographs showing the manner of the ultimate failure of specimens are reproduced in Fig. 9, 10 and 11. Although such information is significant, one does not design for this condition to occur, and it is more important to answer the following two questions:

1. Can steel beams and their connections to columns withstand a sufficient number of cycles of large amplitude, i.e. of load reversals causing severe plastic strains, without breaking during a major earthquake?
2. How dependable is the energy absorption capacity per cycle during severe straining of steel?

An examination of Table 1, bearing in mind the exceptional severity of the imposed strains in the reported experiments, provides an affirmative answer to the first question. With the exception of two defectively fabricated specimens, for each specimen the number of cycles before failure occurred was quite large in relation to what might be anticipated during a severe earthquake.

An examination of the hysteresis loops is necessary to answer the second question. Three sequences of hysteretic loops from one of the experiments are shown in Fig. 12. Their remarkable repetitiveness and reproductibility during a number of consecutive identical cycles is noteworthy. Experimental evidence also clearly demonstrates that the onset of flange buckling does not cause the capacity of the beam to deteriorate significantly. The gradual work-softening which may be noted from Fig. 12 appears to be of no importance in seismic design as it occurs only after an excessively large number of load reversals.

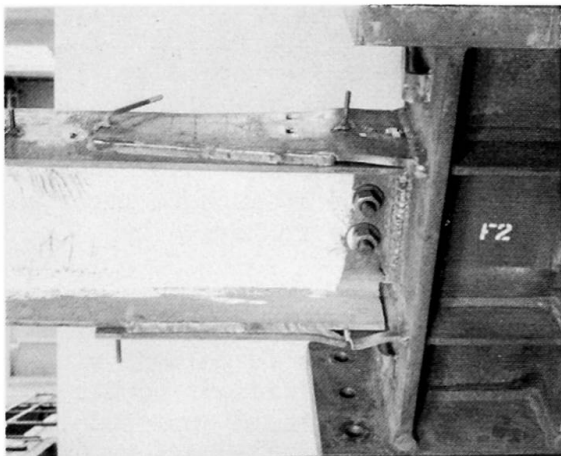


Fig. 10

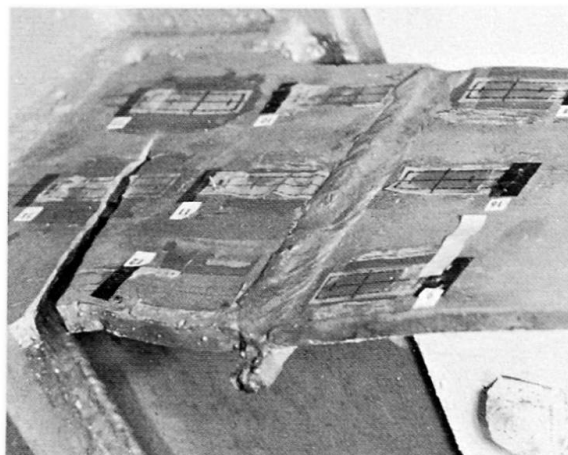


Fig. 11

The completed experiments further provided good evidence on the increase in the size of the hysteresis loops with increasing deflections. This is illustrated in Fig. 13. An approximate linear relationship between the area enclosed by the hysteresis loops with the increasing plasticity ratio has been proposed (4, 5). Therefore, on the basis of the experimental evidence, it appears that the reliability of the energy absorption capacity of properly designed and fabricated structural steel beams and their connection, is assured.

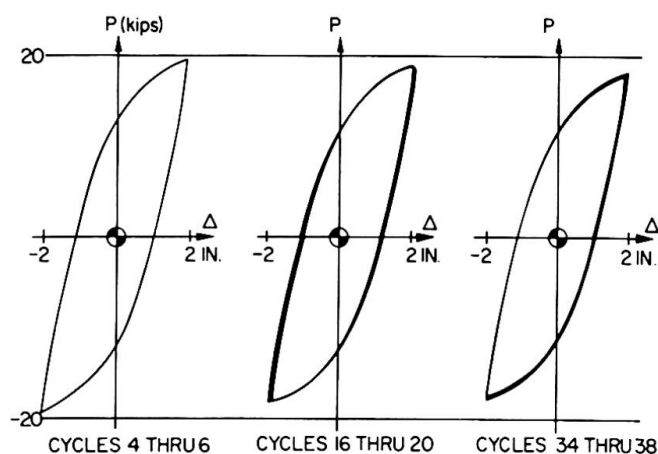


Fig. 12 Specimen F2-C4

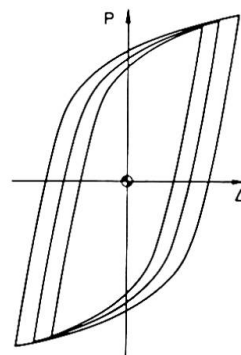


Fig. 13

Application of Experimental Results

Once one is satisfied that the hysteresis loops are reproducible during consecutive identical cycles of load application, and that the increase of the loops with increasing deflections is reasonably well established, this information can be put in mathematical form suitable for the analysis of structures. The well-known Ramberg-Osgood representation of non-linear load-displacement relationships together with Masing's hypothesis provide suitable mathematical formulations (5, 9).

Precisely this type of idealization has been applied by Berg (10) to some of the hysteresis loops generated in these experiments. By using such a formulation he studied the response of the assumed structure to a very severe ground motion are shown in Fig. 14(a), (b) and (c). The same results superposed on the same graph are shown in Fig. 15. The lateral displacements for the assumed structure having one degree of freedom are shown in Fig. 16 for a longer period of time. From this figure it is seen that often the displacements are not as severe as shown in Fig. 15 and are essentially elastic in their character.

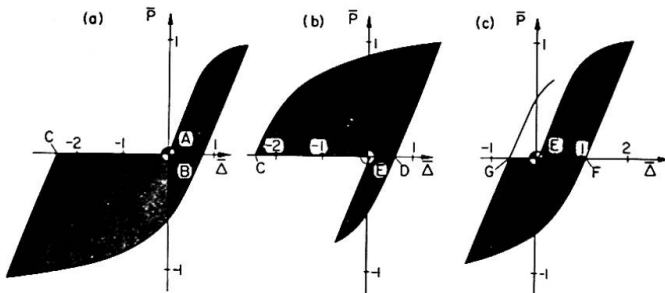


Fig. 14

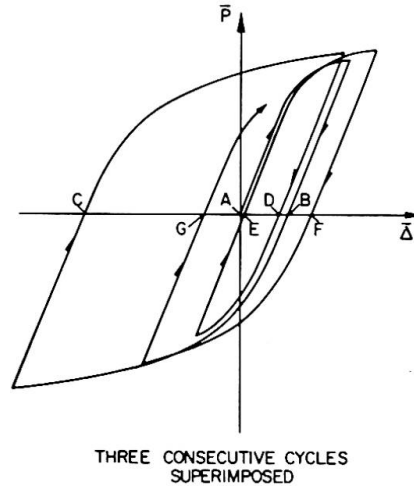


Fig. 15

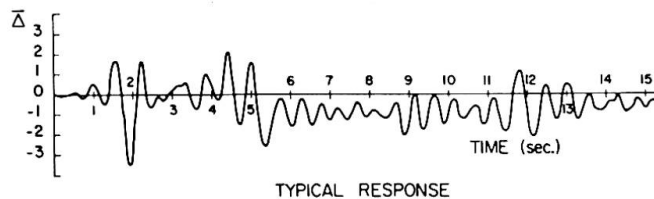


Fig. 16

Studies such as made by Berg for the above simple problem are the kind that are needed for real structures. From such studies the behavior of any one connection can be determined for an assumed earthquake. The amount of energy to be dissipated (shaded areas in Fig. 14) could be found and an assessment of the adequacy of the joint be made. Such a procedure would place the aseismic design of buildings on a more rational basis.

Acknowledgements

The work reported in this discussion was sponsored by the American Iron and Steel Institute. Among the number of people who have participated in this program, the writer is particularly indebted to R. B. Pinkney, a graduate student at the University of California, who participated in all phases of this investigation.

References

1. Bertero, V. V., and Popov, E. P., "Effect of Large Alternating Strains on Steel Beams", J. of Struct. Division ASCE, Vol. 91, ST1, Feb. 1965, pp. 1-12.
2. Popov, E. P., and Franklin, H. A., "Steel Beam-to-Column Connections Subjected to Cyclically Reversed Loading", Proceedings 34th Annual Convention, Struct. Eng. Assoc. of California, October 1965, pp. 79-86.
3. Popov, E. P., "Low-Cycle Fatigue of Steel Beam-to-Column Connections", Internat. Symposium on The Effects of Repeated Loading of Materials and Structural Elements, Mexico City, 1966, Vol VI.
4. Popov, E. P., and Pinkney, R. B., "Behavior of Steel Building Connections Subjected to Repeated Inelastic Strain Reversal-Experimental Data", University of California, Berkeley, SESM 67-31, December 1967.
5. Popov, E. P., and Pinkney, R. B., "Alternating Inelastic Strains in Steel Connections", J. of Struct. Division ASCE, (in preparation).
6. Popov, E. P., "Reliability of Steel Beam-to-Column Connections under Cyclic Loading", Fourth World Conference on Earthquake Engineering, Santiago, Chile, January 1969, (in preparation).
7. Courtesy of Professor Joseph Penzien.
8. Current AISI Project 145 under the supervision of V. V. Bertero and E. P. Popov.
9. Jennings, P. C., "Periodic Response of a General Yielding Structures", J. of Eng. Mech. Division ASCE, Vol. 90, FM2, April 1964, pp. 131-166.
10. Berg, G., "A Study of the Earthquake Response of Inelastic Systems", Preliminary Reports - Steel Research for Construction, February 1966, AISI.

SUMMARY

In this discussion attention is called to the availability of some of the new experimental results on the inelastic behavior of steel cantilever beams and their connections to column stubs during repeated and reversed cyclic loading. The described experiments attempt to simulate the conditions which develop in structural steel frames during an earthquake.

RÉSUMÉ

Cette contribution signale l'existence de nouveaux résultats expérimentaux concernant le comportement inélastique de poutres consoles en acier et leur liaison à des colonnes courtes soumises à des charges périodiques répétées et alternées. Le but des expériences décrites est de simuler les conditions qui se développent dans des ossatures en acier pendant un tremblement de terre.

ZUSAMMENFASSUNG

In diesem Beitrag soll auf einige der neueren experimentellen Ergebnisse über das inelastische Verhalten von Kragträgern aus Stahl aufmerksam gemacht werden, sowie ihren Anschlüssen an Stützenabschnitte, wenn die Träger wiederholten, zyklischen Wechselbelastungen ausgesetzt sind. Anhand der angeführten Versuche wird versucht, die Bedingungen nachzuahmen, die während eines Erdbebens in Rahmenkonstruktionen aus Stahl auftreten.

Leere Seite
Blank page
Page vide