

Behavior of concrete under variable temperature and loading

Autor(en): **Mukaddam, Muhammad**

Objekttyp: **Article**

Zeitschrift: **IABSE reports of the working commissions = Rapports des commissions de travail AIPC = IVBH Berichte der Arbeitskommissionen**

Band (Jahr): **6 (1970)**

PDF erstellt am: **26.05.2024**

Persistenter Link: <https://doi.org/10.5169/seals-7796>

Nutzungsbedingungen

Die ETH-Bibliothek ist Anbieterin der digitalisierten Zeitschriften. Sie besitzt keine Urheberrechte an den Inhalten der Zeitschriften. Die Rechte liegen in der Regel bei den Herausgebern.

Die auf der Plattform e-periodica veröffentlichten Dokumente stehen für nicht-kommerzielle Zwecke in Lehre und Forschung sowie für die private Nutzung frei zur Verfügung. Einzelne Dateien oder Ausdrucke aus diesem Angebot können zusammen mit diesen Nutzungsbedingungen und den korrekten Herkunftsbezeichnungen weitergegeben werden.

Das Veröffentlichen von Bildern in Print- und Online-Publikationen ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. Die systematische Speicherung von Teilen des elektronischen Angebots auf anderen Servern bedarf ebenfalls des schriftlichen Einverständnisses der Rechteinhaber.

Haftungsausschluss

Alle Angaben erfolgen ohne Gewähr für Vollständigkeit oder Richtigkeit. Es wird keine Haftung übernommen für Schäden durch die Verwendung von Informationen aus diesem Online-Angebot oder durch das Fehlen von Informationen. Dies gilt auch für Inhalte Dritter, die über dieses Angebot zugänglich sind.

For designing concrete structures subjected to thermal gradients, the structural engineer requires the complex constitutive time and temperature dependent relations of concrete. Below, a mathematical model is developed which generates the specific compliance surface of concrete for temperatures ranging between 68°F - 200°F, age at loading varying between 28-400 days, and observation time up to 1000 days after loading. The mathematical model is developed for sealed specimen with stress/strength ratio of 35-45% or less.


specific creep = time dependent deformation/unit stress
specific compliance = instantaneous + time dependent deformation/unit stress
thermal strain = $\alpha \Delta T$, where
 α = coefficient of thermal expansion
 ΔT = change in temperature
T.S. material = thermorheologically simple material.

In order to develop the mathematical model the effects of the temperature to which the concrete is subjected to are first studied. Then the effects of age of concrete at loading are discussed separately. Finally the effects of varying the two above parameters simultaneously are determined.

It is demonstrated that concrete under some conditions behaves as a thermorheologically simple material. In order to decide whether a material is T.S. or not one has to check whether all experimental curves of creep at different temperatures fit together by shifting them along the axis of logarithmic time.

Then as seen from Fig. 1,

or $\ln(t)$ for T curve corresponds to $(\ln(t) + \psi(T))$ for the T_0 curve. Thus t for T curve corresponds to $\text{Exp}(\ln(t) + \psi(T))$ for T_0 curve, but $\text{Exp}(\ln(t) + \psi(T)) = t \text{Exp}(\psi(T))$ call $\text{Exp}(\psi(T)) = \phi(T) \equiv$ shift function for temperature T having T_0 as reference temperature.

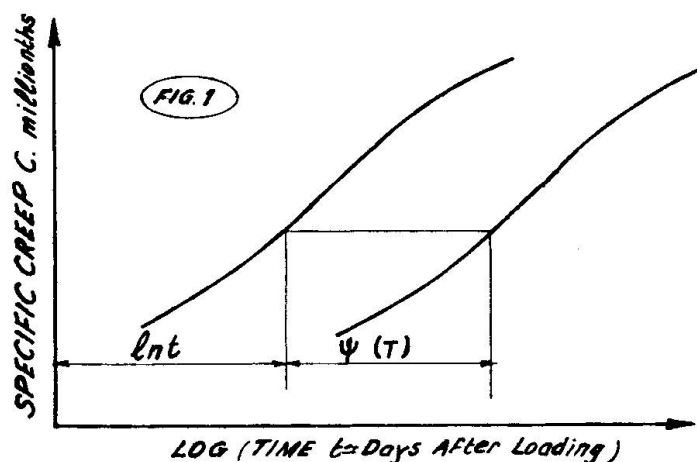

Hence knowing the specific creep curve at one temperature for T.S material one can determine the specific creep curves for that material at any other constant temperature T , by simply replacing the argument t in reference curve by $t \phi(T)$.

The number of reliable published experimental results on creep characteristics of concrete at high temperatures is limited. Using the available data it is demonstrated that concrete behaves as a T.S material for temperatures between 60 - 200 °F and age at loading of 10 days or more.

A.D. Ross (Ref 1) presented data for total strain (elastic + creep)/ksi for uniaxial cylinders loaded for 80 days at different temperatures ranging from 68°F to 284°F.

All specimens were sealed and loaded at an age of 10 days. Also included in the data is the instantaneous response on loading for different temperatures. Fig. (2) shows how good the fit is for different temperatures, ranging from 68°F - 176°F.

Another independent set of data is obtained from Ref.(2) by D. Hannant. In this case concrete was cured for 24 hours under wet sacks before demolding, followed by five months under water at 20°C (68°F) and one month in the sealed saturated condition. The temperature range that the concrete was subjected to, is 27°C - 77°C (80.6-170.6°F). Figure (3) shows that the shift principle leads to accurate results in this case.

Effect of Age at Loading:


It is known that specific creep is a function of age at loading. Recently, research has been done on the mathematical form of the function representing the variation in the specific creep with a change in the age at loading of concrete.


After close examination of the shapes of the specific creep curves at different ages of loading, and keeping in mind that the rate of chemical reaction in concrete is affected by temperature as well as by time, the following is proposed:


$$\text{If } C(K_0) = \sum_{i=1}^n C_i e^{-\lambda_i t}$$

represents the specific creep at a certain reference age at loading K_0 ,

where C_i , λ_i are constant coefficients, and t is time in days after loading.

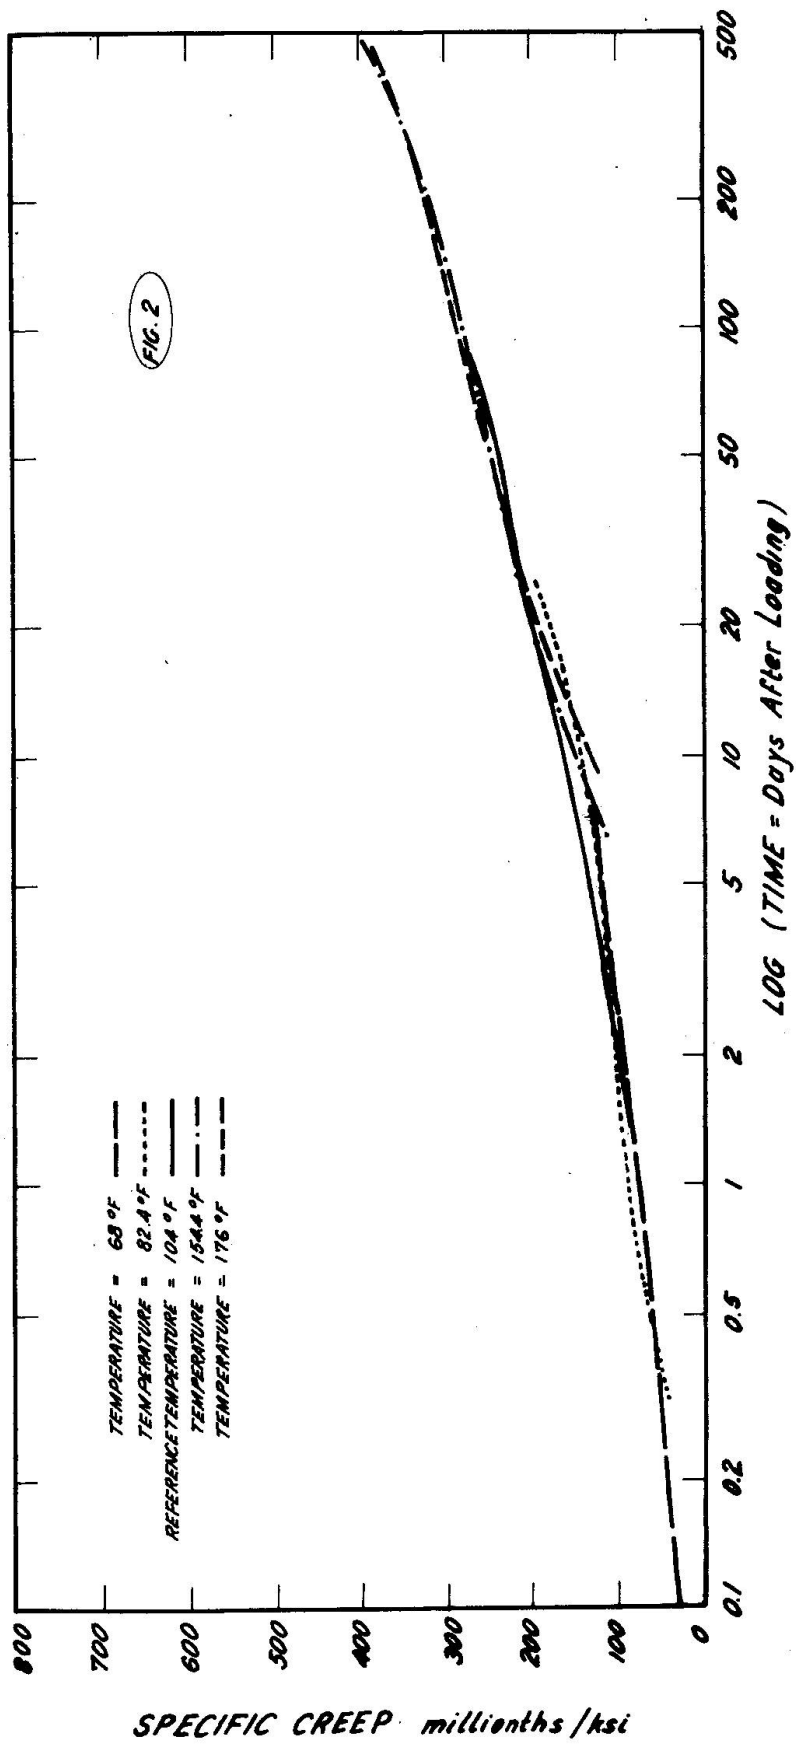

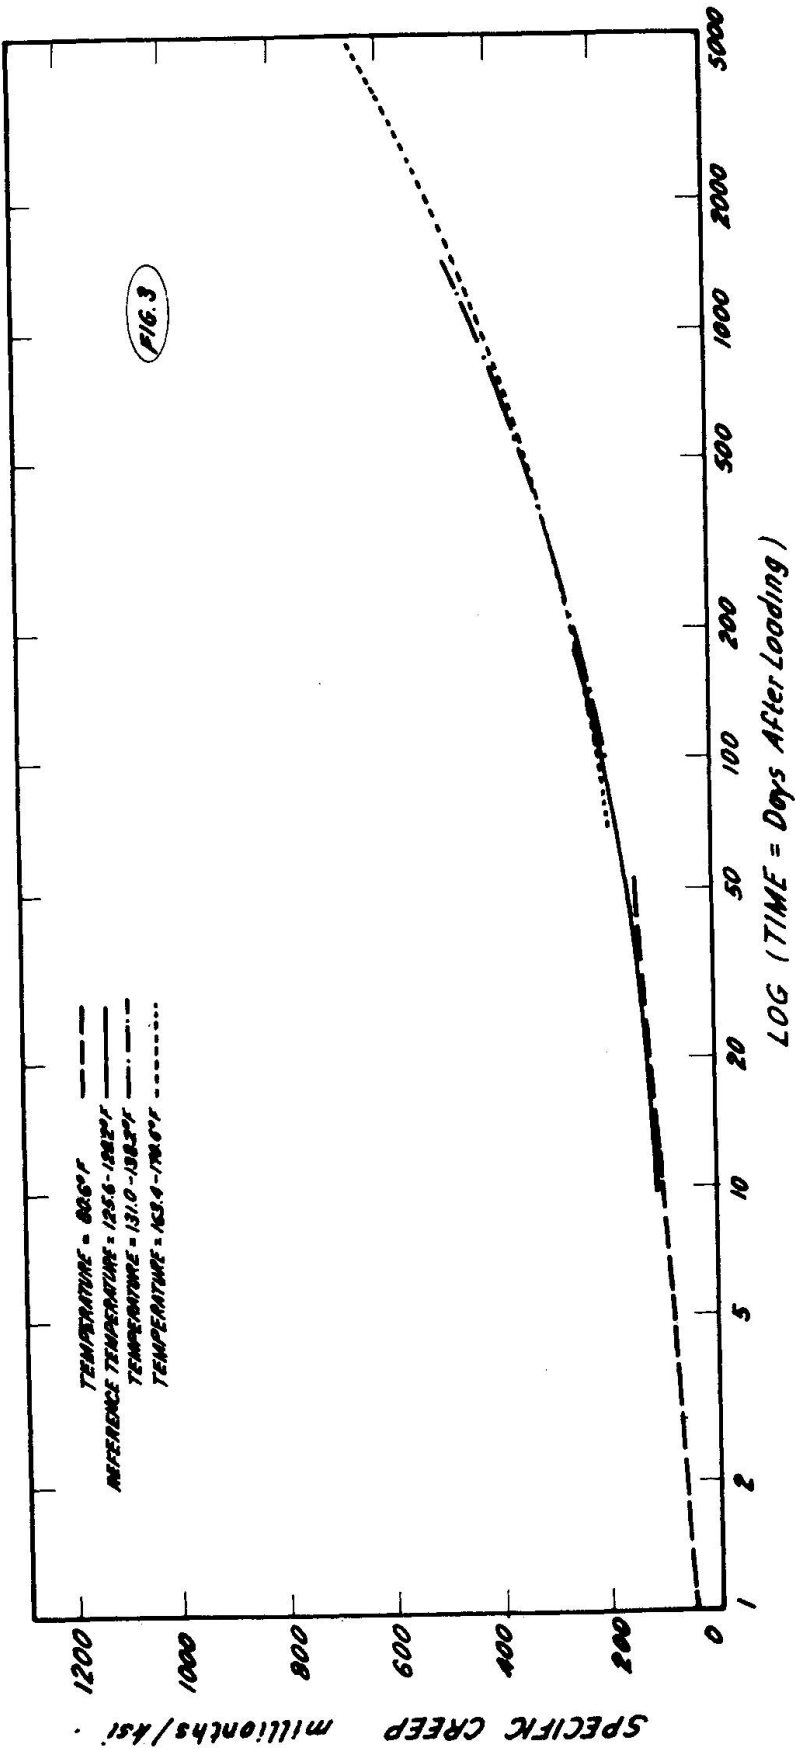

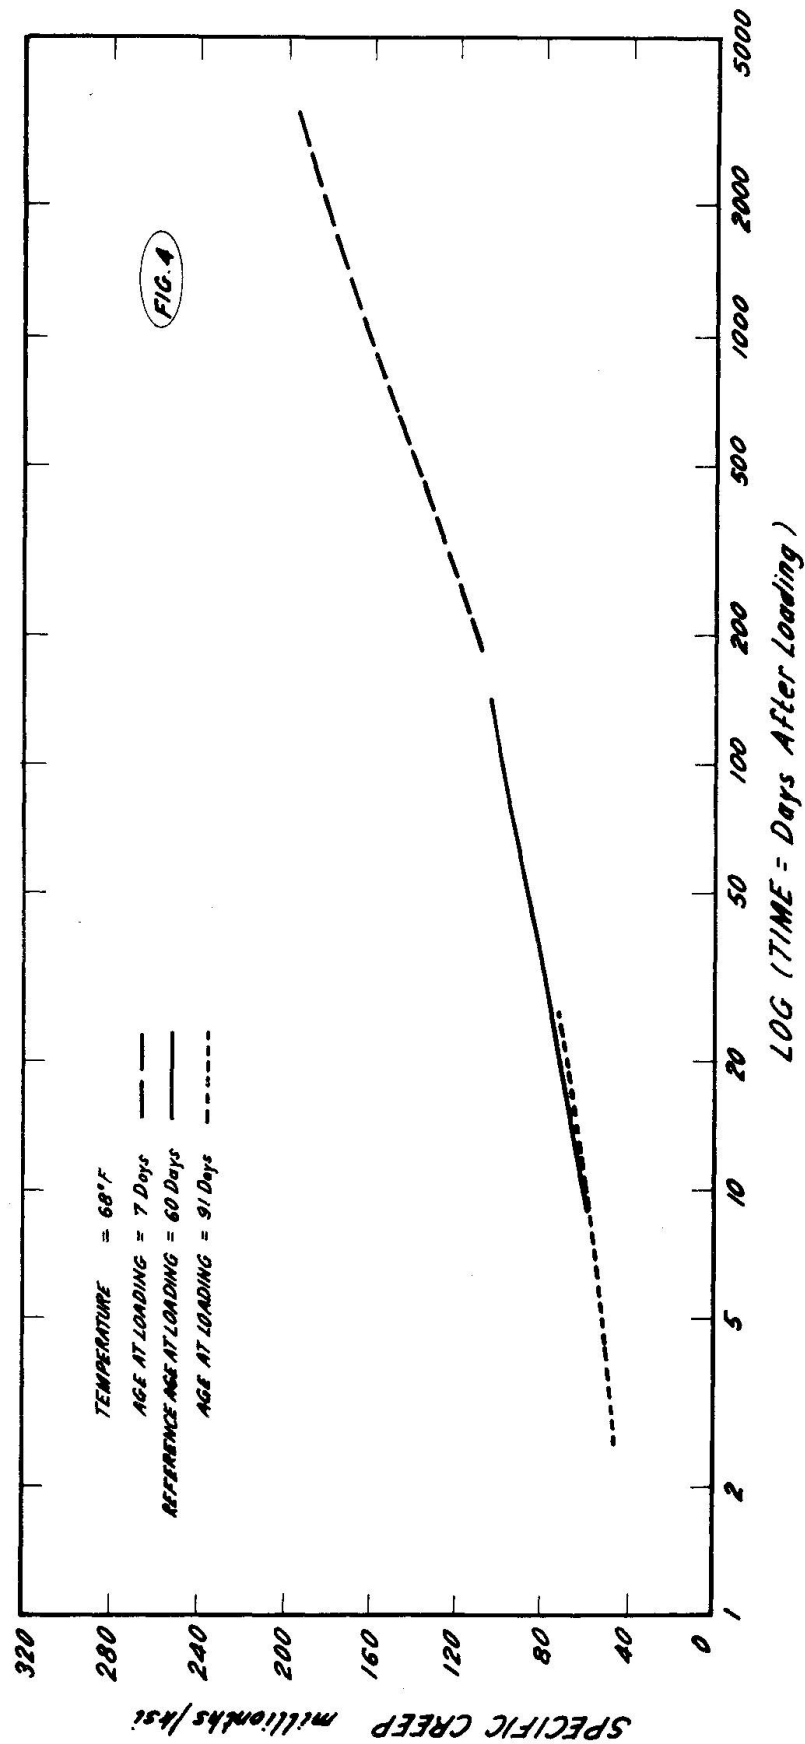

$$\text{then } C_{(K)} = \sum_{i=1}^n C_i e^{-\lambda_i t} \psi_i(K)$$

represents the specific creep of the concrete loaded at a different age K . This is similar to temperature shift function principle.

$\psi_i(K)$ is the shift function for ageing of the concrete.

To check the validity of this proposal, the same data used by Selna Ref. (3) and presented by A. Ross (4) is used. Figures (4,5) show how good the proposed model is. In addition to giving good results, this method is simple to apply, gives better interpolation values than Selna's Model, and much better extrapolation values for specific creep. This principle leads to a compatible formulation for the simultaneous consideration of temperature and age at loading on the creep characteristics of concrete.

Combined Effects of Temperature and Ageing on Creep Characteristics of Concrete:


If temperature and age at loading of concrete were independent then the principle of shift function could be applied simply as:

If $C = \sum_{i=1}^n C_i e^{-\lambda_i t}$ represents the specific creep of concrete at reference temperature T_0 and reference age at loading K_0 , then

$C = \sum_{i=1}^n C_i e^{-\lambda_i t} \phi(T) \psi_i(K)$ gives the specific creep for same concrete loaded at an age of K and temperature T .

However, since it is known that age of concrete (maturity) is a function of temperature, the following form of shift function is proposed.

$$TS(K, T) = \phi(T) \psi_i(K, T)$$

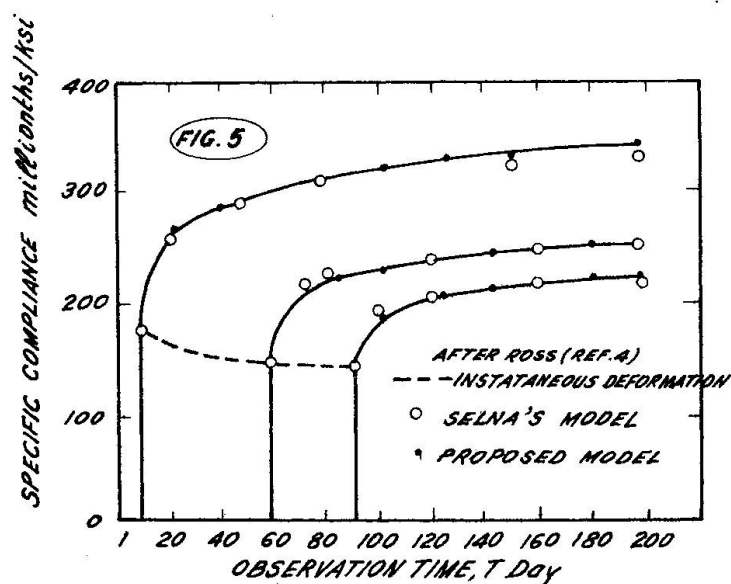

Where $TS(K, T)$ is the total amount the specific creep curve loaded at an age K and temperature T needs to be shifted to fit the reference creep curve.

$\phi(T)$ is the temperature shift function as discussed before.

It is proposed that

$$\psi(K, T) = \psi(\text{COAGE}(K, T))$$

where $\text{COAGE}(K, T) = K_0 + (K - K_0) e^{-A(T - T_0)}$

where K_0, T_0 are the reference age at loading and temperature respectively.

A - is a constant obtained in such a way that the curve $\psi(K, T)$ gives a continuous monotonic curve so that interpolation from such curve is possible.

General Procedure for Finding Shift Functions:

- 1- Calculate the specific creep for each case where $C(t, \tau) =$ specific compliance (t, τ) . Instantaneous strain (τ) , where t is observation time. τ is age at loading.
- 2- Plot all specific creep curves on semi-log papers.
- 3- Select the specific creep curve corresponding to reference age at loading K_0 and reference temperature T_0 as the reference curve.
- 4- By shifting the specific creep curves corresponding to age at loading K_0 and different temperatures T_1, T_2, T_3 etc... determine the temperature shift function $\phi(T)$.
- 5- By shifting the rest of the specific creep curves corresponding to different temperatures and ages at loading so that they fit the reference specific creep curve, determine $TS(K, T)$.
- 6- Determine $\psi(K, T) = TS(K, T) / \phi(T)$ for each specific creep curve.
- 7- By trial and error between steps 7 and 8, determine A such that $\psi_1(\text{COAGE}(K, T))$ will be a smooth monotonic curve. Then determine $\text{COAGE}(K, T)$ for each case as $\text{COAGE}(K, T) = K_0 + (K - K_0) \text{Exp}(A(T - T_0))$.
- 8- $\psi(\text{COAGE}(K, T))$ is determined and plotted.

Thus with the above procedure the specific creep for any temperature and any age at loading can be determined.

Verification of Above Procedure:

There is extremely limited data on the response of concrete loaded at different ages and different temperatures.

R. Browne Ref. (5) presented data for concrete loaded at ages of 28, 60, 180, 400 days and for each age some specimens were subjected to 68, 104, 149 and 200°F.

For this concrete, the specific creep curve corresponding to age at loading 28 days and temperature 68°F is chosen as reference. The equation which represents the reference curve is found.

$$C(28, 68) = 919.01 - 46.27 e^{-.2t} - 95.08 e^{-.02t} - 156.32 e^{-.002t} - 197.60 e^{-.0002t} - 370.22 e^{-.00002t} \quad (1.a)$$

where t is time in days after loading.

The shift function $\phi(T)$ is found in this case to be

$$\phi(T) = -3.55 \left(\frac{T}{68}\right)^3 + 21.57 \left(\frac{T}{68}\right)^2 - 33.83 \left(\frac{T}{68}\right) + 16.79 \quad (1.b)$$

where T is temperature in $^{\circ}\text{F}$.

$\phi(T)$ is temperature shift function.

Also it is found that in this case

$$\begin{aligned} \text{COAGE (K,T)} &= K_0 + \sum_{i=1}^n \Delta K(i) e^{-A(T(i)-T(0))} \\ \text{or COAGE (K,T)} &= 28. + \sum_{i=1}^n \Delta K(i) e^{-0.6(T(i)-68)} \end{aligned} \quad (1.c)$$

where $(K_0 + \sum_{i=1}^n \Delta K(i))$ gives actual age of concrete in days if no corrections for temperature, or temperature history are applied.

$$\begin{aligned} \psi_1 (\text{COAGE (K,T)}) &= .056 + .686 e^{-.01(\text{COAGE (K,T)})} \\ \text{for COAGE} &\geq 28.3 \text{ days} \end{aligned} \quad (1.d)$$

The instantaneous deformation / ksi is found as a function of age at loading and temperature.

$$\begin{aligned} \text{Instantaneous def. } (\tau)/\text{ksi} &= 210. \left\{ -.086 \left(\frac{T}{68}\right)^3 + .352 \left(\frac{T}{68}\right)^2 - .019 \left(\frac{T}{68}\right) + \right. \\ &\quad \left. .753 \right\} + \frac{1600}{\tau} \end{aligned} \quad (1.e)$$





where τ is the times at loading in days
 T is temperature in $^{\circ}\text{F}$.

Using the above mathematical Model equations (1.a - 1.e) the total deformation/ksi for all the cases are computed and plotted as shown in Figs. (6.a - 6.d).

The results fit well with the experimental results if one considers the accuracy of results of experimental work Ref.(5).

To illustrate the capability of the mathematical model two examples in which simple uniaxial concrete cylinders are subjected to different loads and temperatures are solved. Also, a study of the behavior of a concentrically prestressed concrete beam subjected to thermal gradients is done. Finally, in order to simulate the nuclear reactor pressure vessel, a thick-wall ring structure subjected to internal thermal gradients, internal pressure and external pressure (Prestressing) is analyzed.

Incremental approach using finite element method is used in the solution of these structural problems. It is only for the lack of space that the results of these examples shall not be included here.

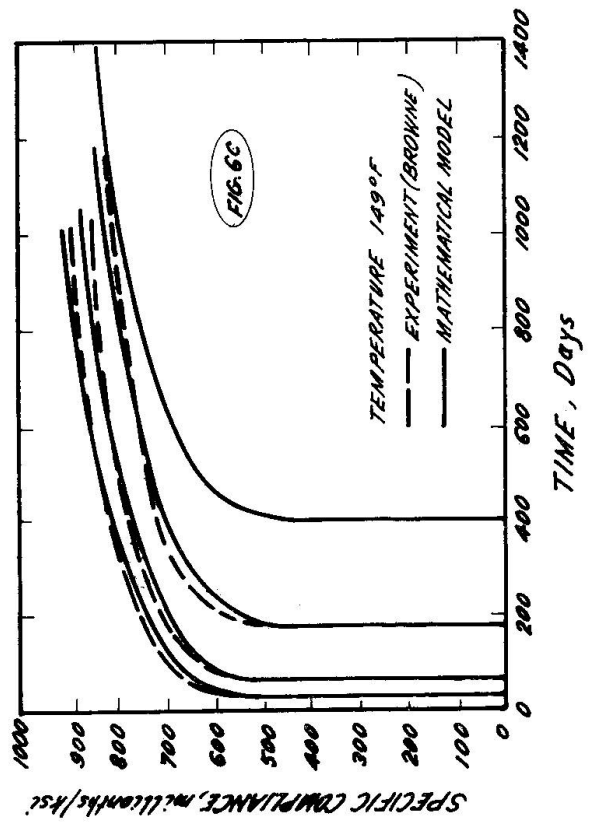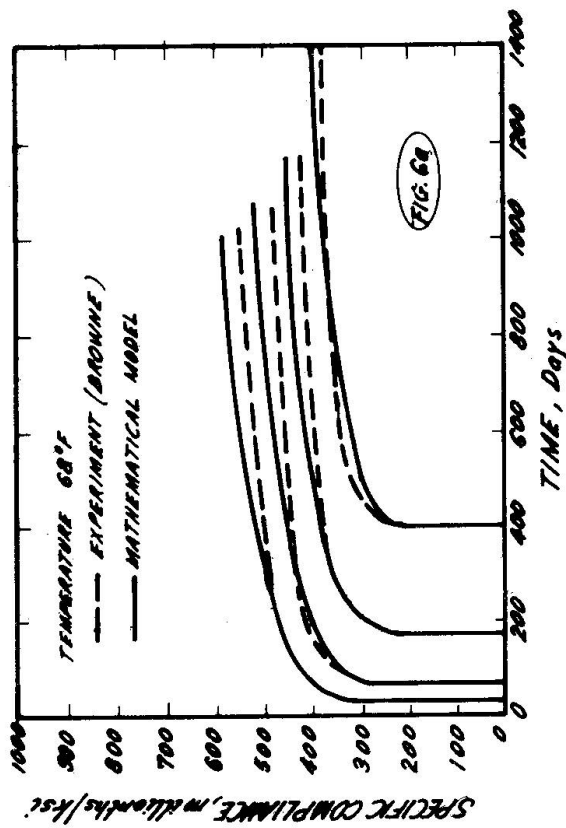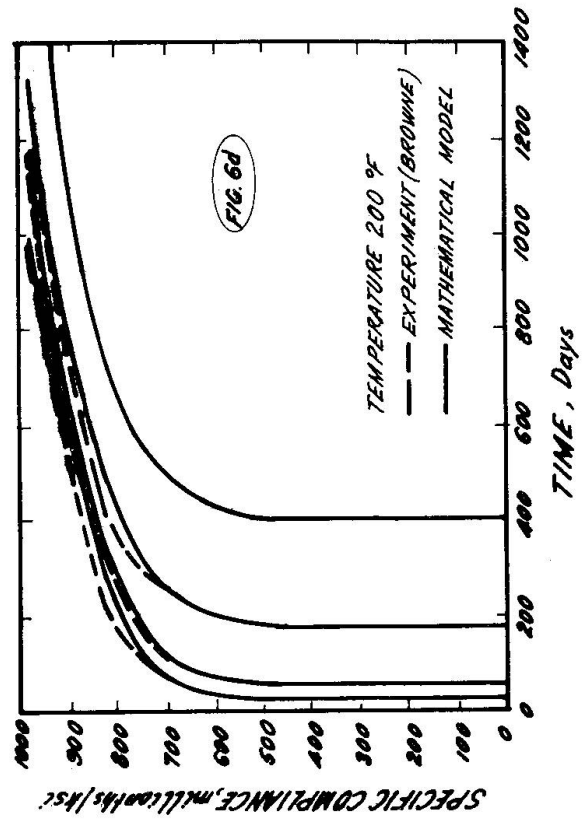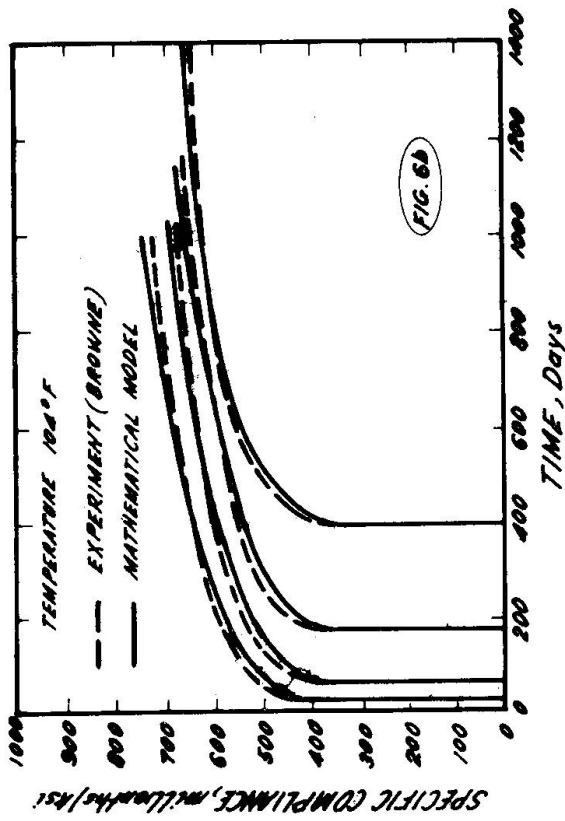

References:

- 1- A. Ross, "The Influence of Sustained Temperature on the Shrinkage and Creep of Concrete and the Effects in Some Structures", Colloquium on the Nature of Inelastic Behavior of Concrete and its Structural Effects, Cornell University, June 1965.
- 2- D. Hannant, "Strain Behavior of Concrete Up to 95°C Under Compressive Stresses", Proc. of Conferences on Prestressed Concrete Pressure Vessel, Group C, Paper 17, London 1967.
- 3- L. Selna, "Time - Dependent Behavior of Reinforced Concrete Structures", SESM Report No. 67, 19 August 1967, University of California, Berkeley.
- 4- A. Ross, "Creep of Concrete Under Variable Stress", Proc. ACI, Vol. 54, 1958, pp. 739-757.
- 5- R. Browne, "Properties of Concrete in Reactor Vessels", Proc. of Conference on Prestressed Concrete Pressure Vessel, Group C, Paper 13, London 1967.

* * *