

**Zeitschrift:** IABSE reports of the working commissions = Rapports des commissions de travail AIPC = IVBH Berichte der Arbeitskommissionen  
**Band:** 23 (1975)  
**Artikel:** The European column curves  
**Autor:** Beer, H. / Schulz, G.  
**DOI:** <https://doi.org/10.5169/seals-19828>

### **Nutzungsbedingungen**

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

### **Conditions d'utilisation**

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

### **Terms of use**

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

**Download PDF:** 02.07.2025

**ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>**

## THE EUROPEAN COLUMN CURVES

H. Beer (†) and G. Schulz  
Technical University Graz

### ABSTRACT

The column curves adopted by Commission 8 (Stability) of the European Convention of Constructional Steelwork are the result of a comprehensive program of experimental and theoretical investigations. The reduction of the load carrying capacity through geometrical imperfections of the strut, as initial out-of-straightness, and through material inhomogeneities, as residual stresses and scatter of the yield point, were systematically investigated. The theoretically predicted column curves were compared with the results of a statistical evaluation of the column tests and show close agreement.

In addition to the 3 column curves adopted by Commission 8, two more curves, an upper and a lower one are suggested for future use. The upper curve should be used for certain shapes made of high strength steels, and the lower curve for heavy shapes ("Jumbo" shapes).

## 1. INTRODUCTION

The theoretical analysis of the strength of steel columns guided by Commission 8 (Stability) of the European Convention of Constructional Steelwork had three major objectives:

The systematic study of the main factors that influence the column strength, as shape of the cross section, geometric imperfections, and material inhomogeneities.

The selection of representative column strength curves for various column types.

The comparison of the theoretical column curves with test results.

The computer program developed for the maximum strength analysis considers the structural member with imperfections (Fig.1). Geometric imperfections are an initial curvature of any given form, and end excentricities of the axial load. Besides the axial load there can be additional small transversal loads. Residual stresses and the variation of the yield stress over a given cross section are taken into account when the relationship between axial load, moment, and elastic-plastic bending stiffness is calculated.

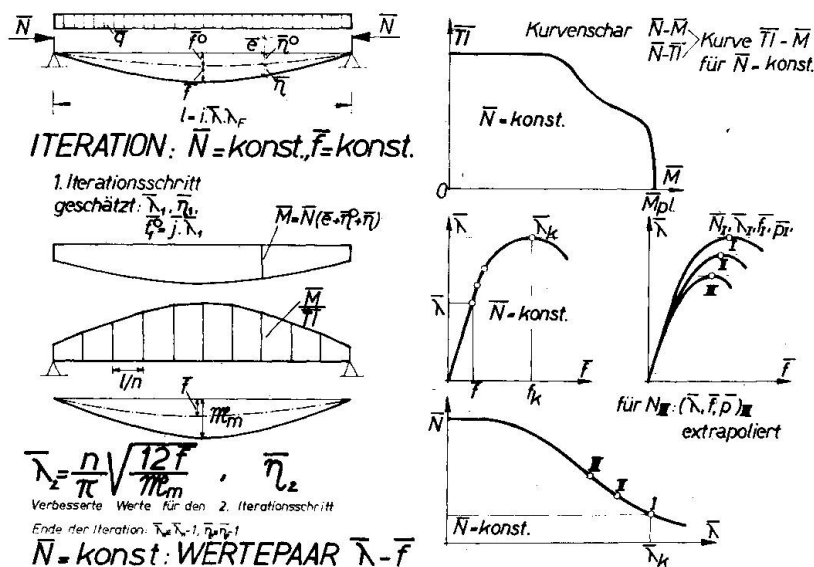


Fig.1: Maximum strength analysis of a structural member with imperfections

It is assumed that the limit of the load carrying capacity is reached, when the equilibrium between external and internal forces changes from a stable to an unstable condition. Since out of practical reasons the calculation is done for a constant axial load  $N$ , but a variable slenderness

$\lambda$ , the limiting state is defined by the vertex in the curve slenderness  $\lambda$  versus central deflection  $f$ . For the limit slenderness  $\lambda_K$  the given axial load  $N$  becomes then the maximum strength.

The calculation of the column curve axial load  $N$  versus slenderness ratio  $\lambda$  starts in the so called "elastic" range and proceeds automatically until the yield load is reached.

The column curves are plotted in the usual non-dimensional diagram.  $\bar{N}$  is the axial load  $N$  related to the yield load.  $\bar{\lambda}$  is the non-dimensional slenderness ratio.

A detailed description of this maximum strength analysis is contained in Ref.(1) and (2).

## 2. GEOMETRIC IMPERFECTIONS

As a first step of the investigation it was analysed to which extend the unintentional load excentricity due to manufacturing methods can be simulated by an initial curvature with the shape of a half-sine wave.

The measurements on columns of the European experimental program indicated a variety of curvatures. Besides antimetric shapes, some columns had their maximum out of straightness rather in the quarter points than in the center. As Fig.2 shows, such a curvature can be approximated with sufficient accuracy by the first coefficient of a Fourier series. For a curvature with an out of straightness of  $\ell/650$  near the quarter points, the substitute half sine-curve has a central bow of  $\ell/1000$ . The column curves calculated for both curvatures are in good agreement.

Based on this approximation, the substitute central bows for all European test columns were calculated and are shown in Fig.3 as function of the column length  $\ell$ . The most unfavorable values for each column type vary from  $\ell/530$  to  $\ell/3360$ . Also shown in this table are measurements on a truss bridge over the Danube: Here  $\ell/1100$  was the largest eccentricity.

Since eccentricity limits are stated in several European building codes,  $\ell/1000$  was choosen as reasonable assumption for the central bow of the initial curvature.

To which extend covers an initial curvature with  $\ell/1000$  unintentional end eccentricities? (Fig.4) For a wide flange I section the magnitude of the end eccentricity was choosen as function of the radius of inertia  $i$ . With  $i/40$ ,  $i/20$  and  $i/10$ , these assumptions cover for this particular section an eccentricity range from 1,25 mm to 4,98 mm. Eccentricities that are unintentional can be expected to fall within the range covered by the first two curves. As Fig.4 shows, the column curve calculated with  $\ell/1000$  covers most of these end eccentricities in the slenderness range of practical interest.

How does a variation and in particular a reduction of  $\ell/1000$  as central bow effect the column strength. In Fig.5 column curves are calculated for  $\ell/2000$ ,  $\ell/1000$ , and  $\ell/500$  for a wide flange I-section without residual stresses  $\sigma_E$ , and shown with dashed lines for the same section with residual stresses. The comparison shows that the influence of the initial cur-

Darstellung der Vorkrümmung durch Fourier-Reihe:

$f^0 = B_1$  nach Southwell

DIR 20

Knickung schwache Achse

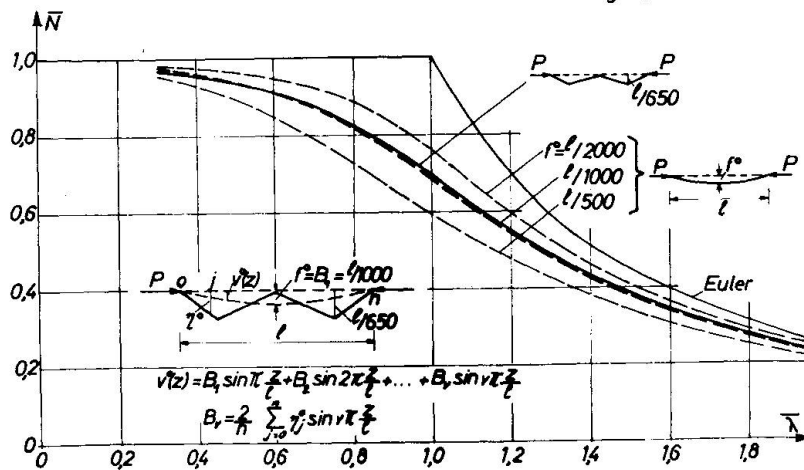


Fig.2: Approximation of an initial out-of-straightness, with maximum in the quarter points, by a Fourier series (I-shape, weak-axis bending)

#### IMPERFEKTIONEN DER VERSUCHSSTÄBE

Profil	Versuchsdurchführung	$\bar{\sigma}^E$	$1/l = 1/f^0$		
			Minimum	Mittelwert	Maximum
IAP 150	Belgien	$\leq 0,125$	590	2100	5100
IPE 160	Deutschland	$\leq 0,3$	2700	4400	7200
IPE 200	Holland	$0,15-0,25$	1390	3800	10000
DIE 20	Belgien	$0,25-0,45$	1690	3700	7600
DIR 20	"	$\leq 0,35(0,5)$	2260	5800	9500
Igeschw	"	$0,45-0,7$	2280	5500	15000
sgeschw	"	$\leq 1,0$	3360		19000
gewalzt	Holland	$\leq 0,5$	1450	2800	5900
$\phi D/t = 18$	"		3050	7000	33000
$\phi D/t = 11$	Deutschland		550	2000	3700
T 60	Holland		1740	5000	9200
TB 60	Deutschland		530	770	1100
Aufmessung Donaubrücke Ingolstadt			1100	5200	13000

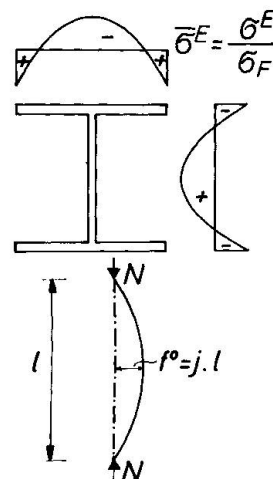


Fig.3: Initial out-of-straightness and residual stress measurements on European test columns

vature decreases with increasing residual stresses. Also, the particular slenderness ratio where the curvature has its maximum influence on the column strength has changed with increasing residual stresses from about  $\bar{\lambda}=1,0$  to about  $\bar{\lambda}=1,3$ .

The reduction of  $1/1000$  therefore will have a different effect on the column strength, dependent on the column type. For sections with high residual stresses the gain of column strength

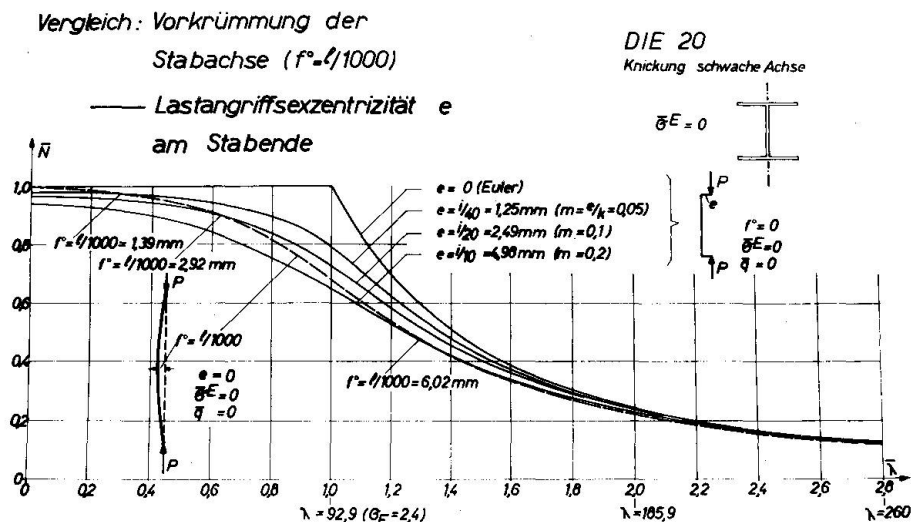


Fig.4: Effect of different geometric imperfections on the column strength (I-section, weak axis bending)

will be small, and will have its greatest influence in a slenderness range that is of no interest for the application of those sections.

All further investigations were based on a column with a sinusoidal initial curvature, with a central bow of  $1/1000$  of the column length.

### 3. SHAPE OF CROSS SECTION AND RESIDUAL STRESSES

For a particular column type -as shown in Fig.6 for I-sections- have size and geometry of the cross section no significant influence on the nondimensional column curve, if we assume the sections to be free of residual stresses.

If we consider the residual stresses typical for each of these rolled I-sections we obtain the wellknown wide scatter of column strength (Fig.7). In particular remarkable is the great reduction of the column strength with increasing residual stresses for weak axis bending. For strong axis buckling is the reduction comparably smaller for those sections that have both, compressive and tensile residual stresses in the flange. For sections with compressive stresses in the flange only the strong axis buckling is equal unfavorable as the weak axis buckling.

# Einfluß der Vorkrümmung

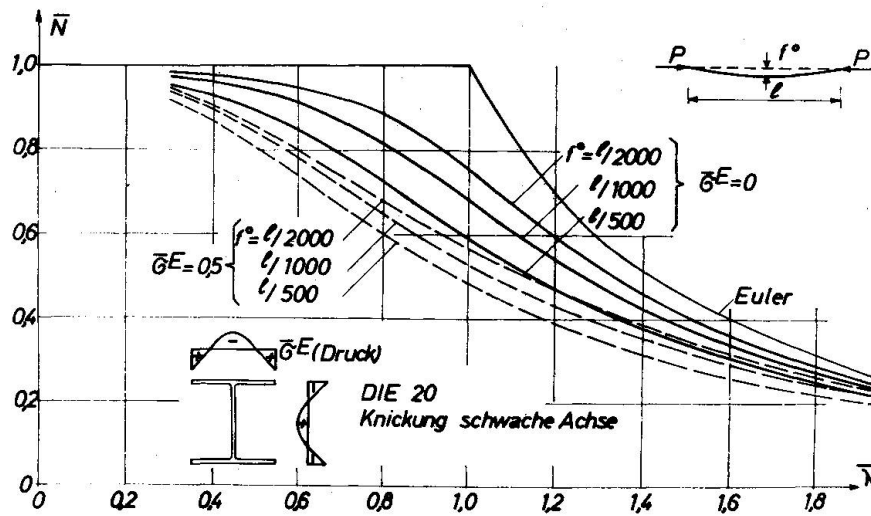


Fig.5: Effect of initial curvature, separately and in combination with residual stresses (I-shape, weak axis bending)

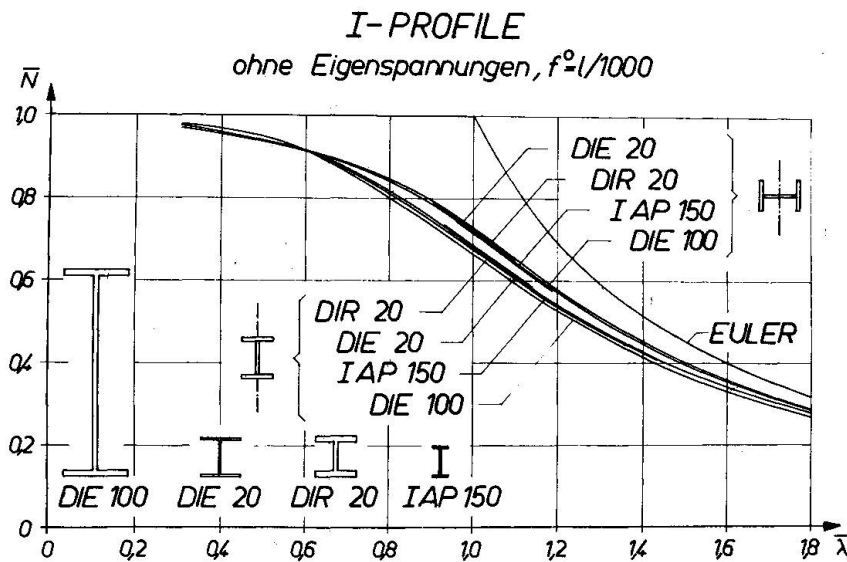


Fig.6: Column strength curves for weak and strong axis bending of I-shapes, including the effect of an initial curvature of  $l/1000$ , but without residual stresses

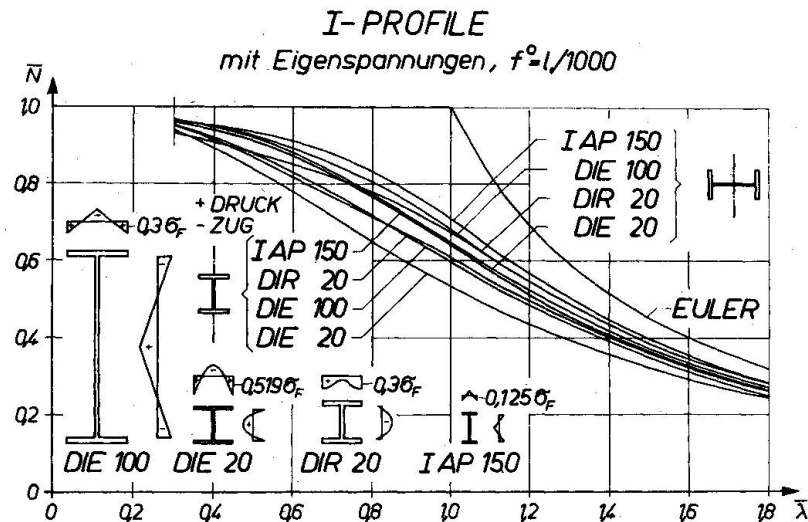


Fig.7: Column strength curves for weak and strong-axis bending of I-shapes, including the effects of an initial curvature of  $1/1000$  and residual stresses

To obtain typical residual stress distributions for those sections most commonly used, residual stress measurements were collected and analyzed. Main sources were the measurements done by Prof. Massonnet in Liège and the results of the research done at Fritz Engineering Laboratory.

The chart in Fig.8 was developed for rolled I-sections as listed in EURONORM, with a flange thickness up to 40 mm. Since the measurements indicated clearly the dependence of magnitude and distribution of the residual stresses from the section geometry, the sections could be arranged in two groups, dependent of the heights over width ratio  $h/b$  smaller or greater than 1,2.  $h/b = 1,2$  is the ratio, where the EURONORM sections change their geometry significantly.

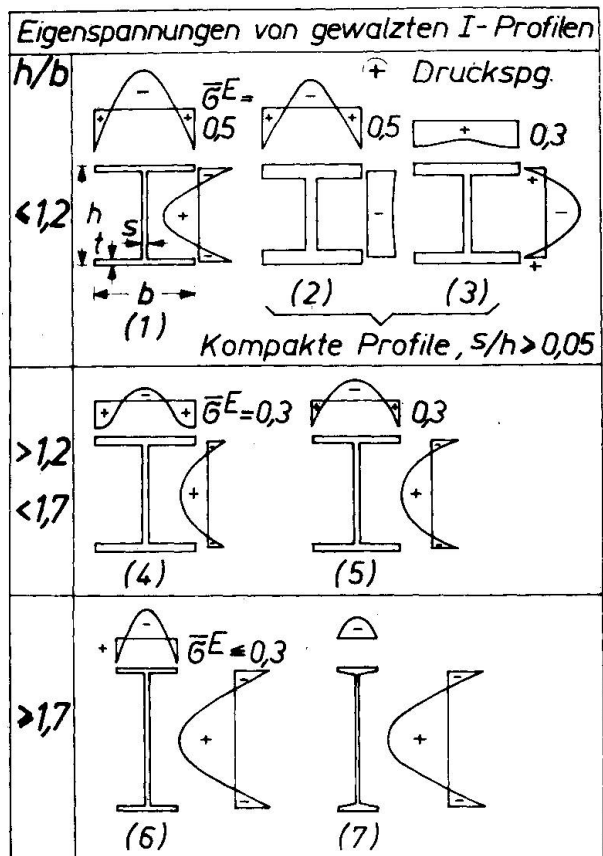


Fig.8: Typical residual stresses for rolled EURONORM I-sections



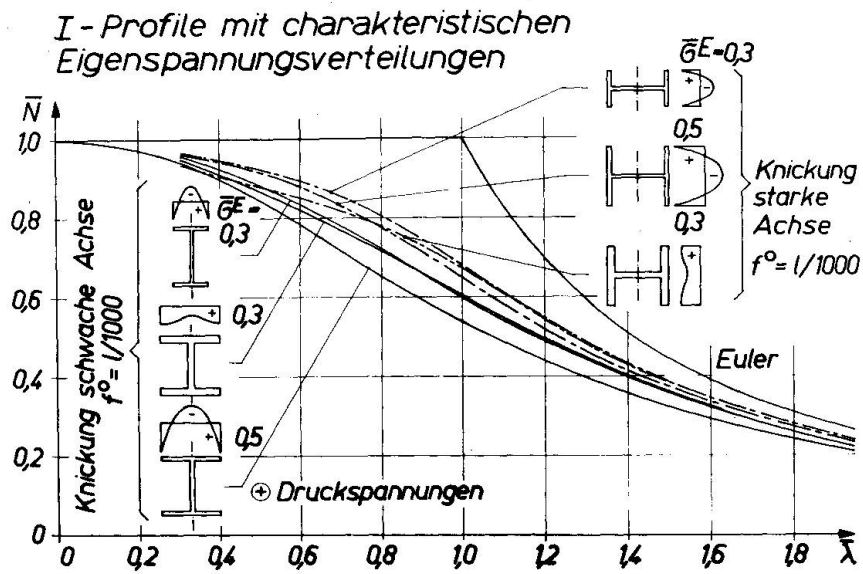


Fig.9: Column strength curves for weak and strong-axis bending of typical rolled I-sections. (Initial curvature  $1/1000$ , residual stresses)

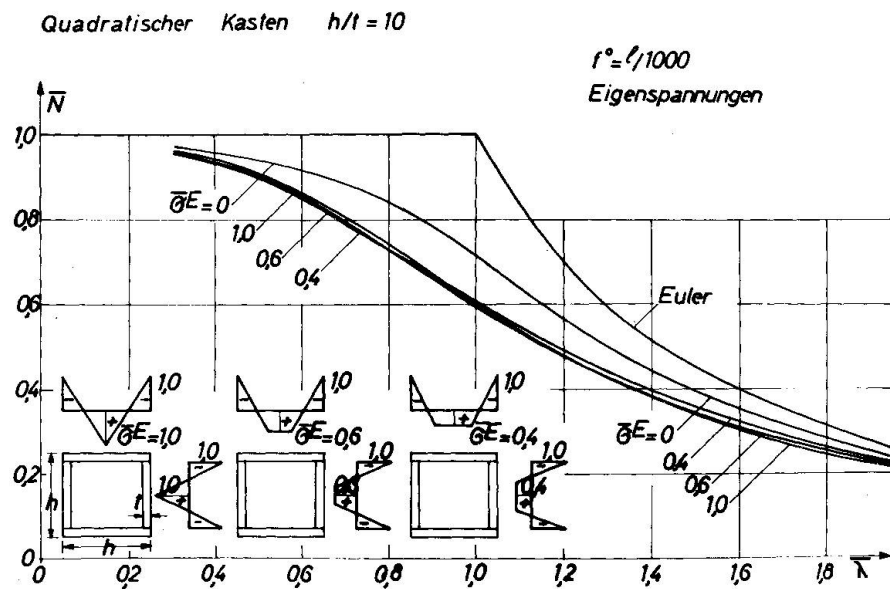


Fig.10: Column strength curves for welded box sections, including the effects of an initial curvature of  $1/1000$  and different residual stress patterns

The column curves for typical sections of the two groups of rolled I-sections, calculated for weak and strong-axis bending, are given in Fig.9. Since it was decided by Commission 8 to recognize a difference in column strength of more than 7%, the strength of rolled I-sections can be represented by 3 column curves.

Part of the investigations that led to the selection of representative column curves for the various sections, was to analyze the effect of a possible variation of a residual stress distribution.

For the welded box sections in Fig.10, the magnitude of the compressive residual stresses in the flange will vary according to the actual size of the section and the amount of welding. This variation had for instance for the residual stress pattern as assumed in Fig.10 no significant influence on the column strength curves.

In Fig.11 this residual stress pattern (marked as E 2) is compared with patterns (E 5 to E 8) that have a wider zone of high tensile residual stresses and recognize the effect of different amounts of welding. They are based on theoretical investigations as outlined in (3), and correspond to box sections with the ratio of height to plate thickness  $h/t$  of 20 and 40, each with a heavy weld (E 5 and E 7) and a light weld (E 6 and E 8). Most of the existing residual stress measurements, done for small and medium sized box sections, actually show patterns that are inbetween E 2 and E 5, E 6, E 7. Pattern E 8 with a width of the compressive stress zone of about 0.9 of the section height will be found only in very wide, thinwalled sections, which are not any more subject to column buckling.

Similar investigations were done for welded I-sections, tubes, and T-sections (1) (2).

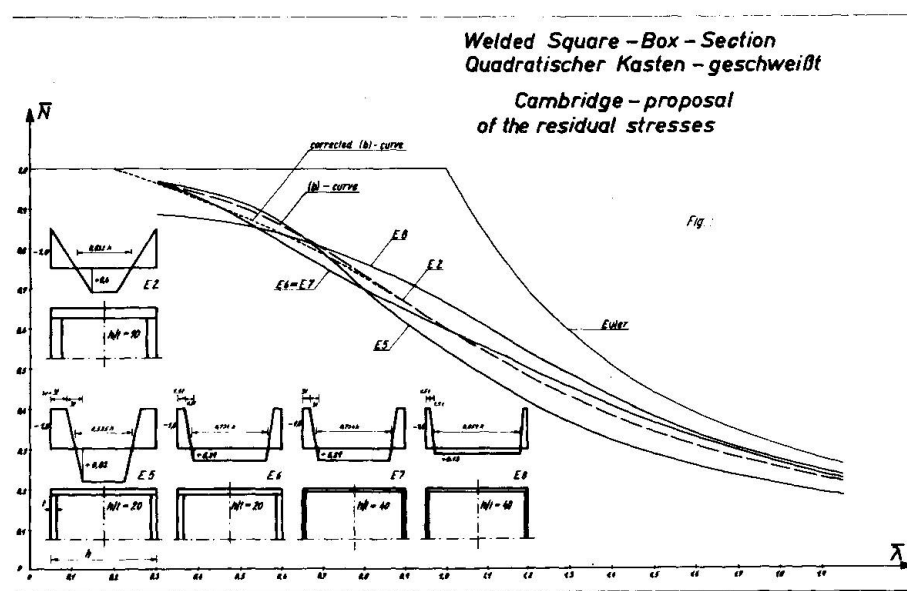


Fig.11: Column strength curves for welded box sections (Initial curvature  $l/1000$ , residual stresses dependent of section size and amount of welding)

#### 4. REPRESENTATIVE COLUMN CURVES

The strength of the most commonly used structural sections could be related to the 3 column curves shown in Fig.12. Curve "a" is the maximum strength column curve for tubes, curve "b" the curve for the box sections, and curve "c" was calculated for the weak axis bending of wide flange I-sections. The other sections are placed in the 3 curves according to Fig.12, as described in detail in (2).

The evaluation of the nondimensional curves "a", "b", and "c" with the appropriate yield stresses is contained in (2), (4) and (5). An approximate method for the design of columns under small transversal loads, based on the curves "a", "b", and "c" is outlined in (6).

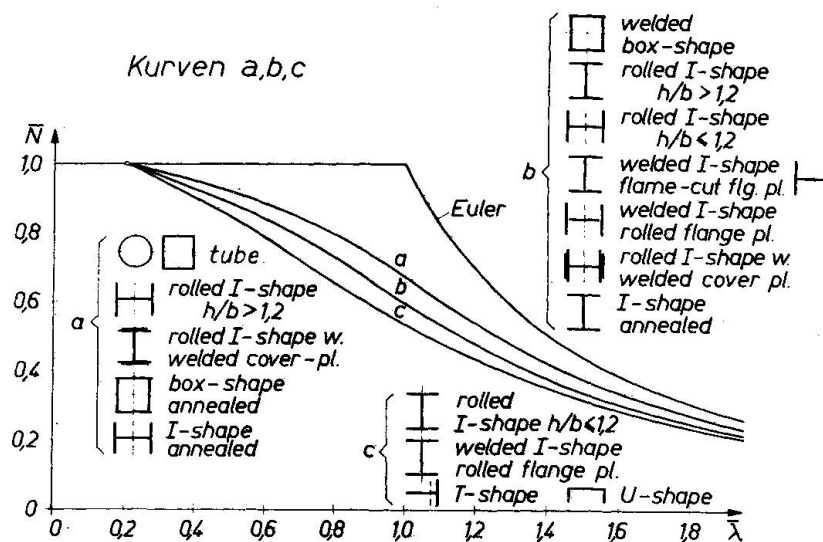


Fig.12: The column curves "a", "b", and "c" recommended by Commission 8 of ECCS

#### 5. COMPARISON WITH TEST RESULTS

The theoretical column curves are in good agreement with the statistically evaluated European column tests (7).

Fig. 13 shows the test results for rolled tubes. The maximum strength as determined out of test results is considered to be the mean value  $m$  minus 2 times the standard deviation  $s$ . For a comparison curve "a", the theoretical curve for tubes, is evaluated with the statistically determined yield stress of the tubes, and is in good agreement with the test results.

The same good agreement can be shown between the test results for the I-sections IPE 160 and the pertinent curve "b" (Fig.14)

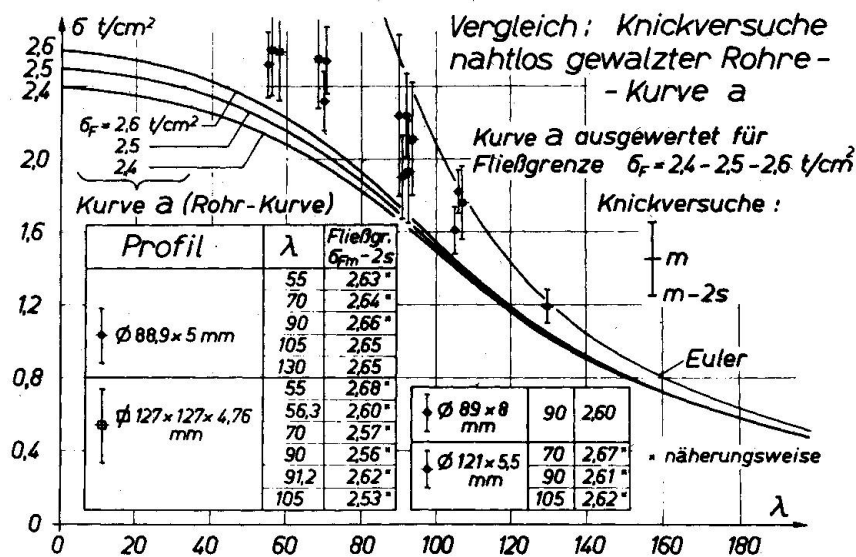


Fig.13: Statistically evaluated tests with rolled tubes and the pertinent column curve "a"

## 6. FUTURE DEVELOPMENTS

The recommended column curves "a", "b", and "c" are slightly conservative for rolled sections of high strength steel, since the reduced influence of the residual stresses due to the higher yield point was omitted. That the omitted gain in column strength is small for the steel-grades presently used in Europe for most rolled sections, can be shown for the case of the weak axis buckling of an I-section. The column curves in Fig.15 are calculated for gradually increasing residual stresses  $\bar{\sigma}^E$ . If we relate these residual stresses to the lowest and highest yield stress of steels presently used in Europe, corresponding parameters would be for instance  $\bar{\sigma}^E = 0.3$  for the lowest yield stress, and  $\bar{\sigma}^E = 0.2$  for the highest yield stress. Although the weak axis buckling is most sensitive to a variation of the residual stresses, the resulting gain of strength is too small, in order to place the section in the next higher of the column design curves "a", "b", or "c".

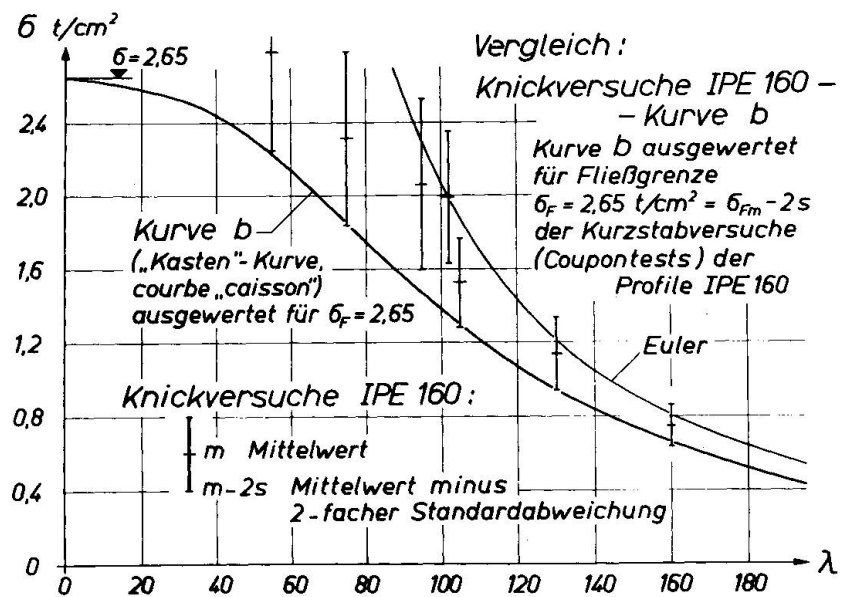


Fig.14: Statistically evaluated tests with I-sections IPE 160 and the pertinent column curve "b"

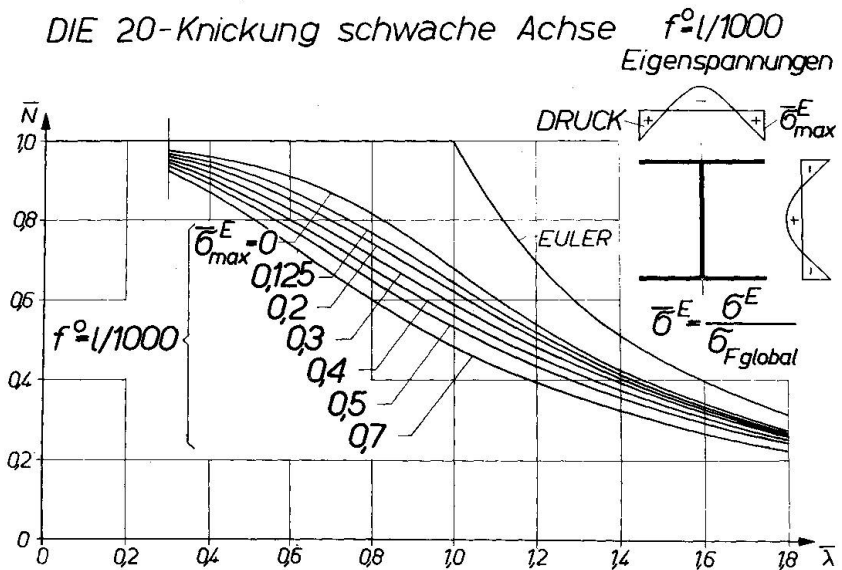


Fig.15: Column strength curves for weak-axis bending of an I-section, including the effects of an initial curvature of  $l/1000$  and gradually increasing residual stresses

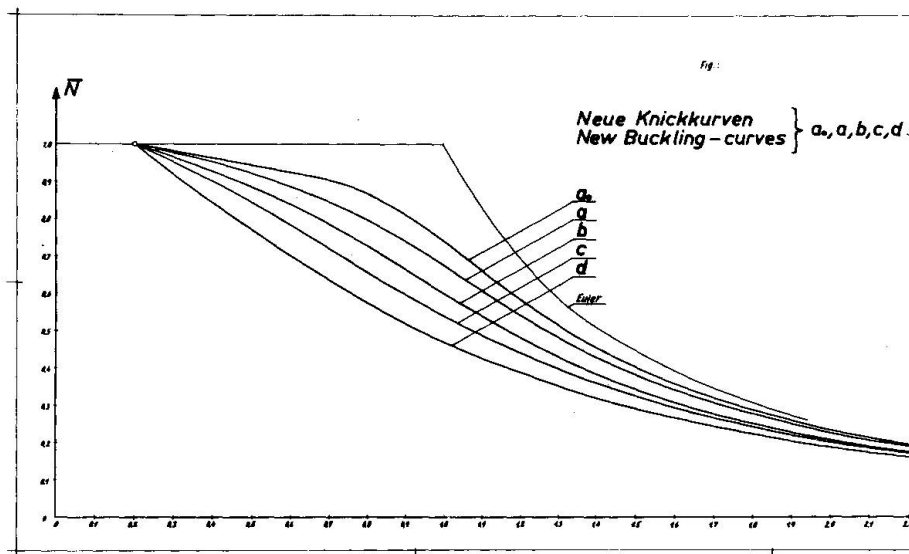


Fig.16: Suggested column curves "a" (for tubes of high strength steel) and "d" (for heavy sections,  $t > 40$  mm)

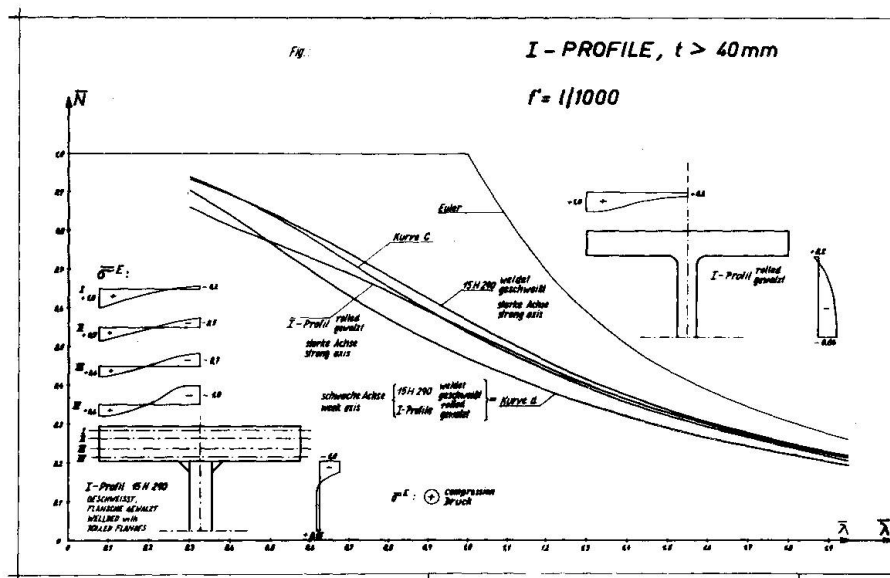


Fig.17: Column strength curves for heavy rolled and welded I-sections. (Initial curvature  $\ell/1000$  residual stresses)

But since steels with a much higher yield point are used more frequently for tubular members, a curve "a<sup>0</sup>" in addition to the curves a, b, c is suggested as future design curve for these sections (Fig.16). Curve "a<sup>0</sup>" was calculated as maximum strength curve for a tubular section without residual stresses.

Finally, as an additional provision for future developments in Europe, a curve "d" is suggested for the design of sections with a wall thickness > 40 mm. (Fig.16). Besides in the United States these heavy sections are already rolled in Great Britain, and might be introduced on the Continent in due time. The column strength curves in Fig.17 are calculated for heavy rolled and welded I-sections, and indicate the need for a design curve lower than curve "c".

#### REFERENCES

- (1) H.Beer and G.Schulz: The Maximum Strength of Axially Loaded Columns with Imperfections. (In German) VDI-Z., Bd. 111(1969), Nr.21, Nr.23 and Nr.24
- (2) H.Beer and G.Schulz: The Theoretical Bases of the New Column Curves of the European Convention of Constructional Steelwork. (In French) Construction Metallique, No.3, September 1970
- (3) B.W.Young and J.B. Dwight: Residual Stresses due to Longitudinal Welds and Flame-Cutting. Cambridge University, Department of Engineering Tech.Report No: CUED/C-Struct/TR.9(1971)
- (4) A.Carpena: Determination of the Yield Point for Column Strength Analysis. (In French) Construction Metallique, No.3, September 1970
- (5) H.Beer and G.Schulz: Flexural Buckling of Centrally Loaded Steel Columns. (In English, French, and German) Report to be published in 1973 by Commission 8 of ECCS.
- (6) G.Schulz: Effect of Transversal Loads on the Ultimate Strength of Struts with Imperfections. (In German) Der Stahlbau, H.4, 1971
- (7) D.Sfintesco: Experimental Basis of the European Column Curves. (In French) Construction Metallique, No.3, September 1970