

# Tunneling Study of High T<sub>c</sub> YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7</sub>-ceramic

Autor(en): **Suzuki, M. / Nishizaki, T. / Rinderer, L.**

Objekttyp: **Article**

Zeitschrift: **Helvetica Physica Acta**

Band (Jahr): **62 (1989)**

Heft 6-7

PDF erstellt am: **24.05.2024**

Persistenter Link: <https://doi.org/10.5169/seals-116147>

## Nutzungsbedingungen

Die ETH-Bibliothek ist Anbieterin der digitalisierten Zeitschriften. Sie besitzt keine Urheberrechte an den Inhalten der Zeitschriften. Die Rechte liegen in der Regel bei den Herausgebern.

Die auf der Plattform e-periodica veröffentlichten Dokumente stehen für nicht-kommerzielle Zwecke in Lehre und Forschung sowie für die private Nutzung frei zur Verfügung. Einzelne Dateien oder Ausdrucke aus diesem Angebot können zusammen mit diesen Nutzungsbedingungen und den korrekten Herkunftsbezeichnungen weitergegeben werden.

Das Veröffentlichen von Bildern in Print- und Online-Publikationen ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. Die systematische Speicherung von Teilen des elektronischen Angebots auf anderen Servern bedarf ebenfalls des schriftlichen Einverständnisses der Rechteinhaber.

## Haftungsausschluss

Alle Angaben erfolgen ohne Gewähr für Vollständigkeit oder Richtigkeit. Es wird keine Haftung übernommen für Schäden durch die Verwendung von Informationen aus diesem Online-Angebot oder durch das Fehlen von Informationen. Dies gilt auch für Inhalte Dritter, die über dieses Angebot zugänglich sind.

Tunneling Study of High  $T_c$   $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$  Ceramic

M. Suzuki<sup>†</sup>, T. Nishizaki,<sup>‡</sup> and L. Rinderer

Institut de Physique Experimentale, Universite de Lausanne, CH-1015 Lausanne, Switzerland

<sup>†</sup>On leave from Saga University, Saga 840, Japan

<sup>‡</sup>Faculty of Science and Engineering, Saga University, Saga 840, Japan

**Abstract:** The Pb-SiO-YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-δ</sub> junctions were fabricated on the ceramic YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-δ</sub> and the V-dI/dV characteristic was measured at temperatures ranging over from 4.4 to 94.1 K, and furthermore under several magnetic fields at 4.4 K. It was found that the temperature dependence of energy gap almost agrees with the one of the BCS theory, and the value of  $2 \Delta_0/k_B T_c$  is 4.06. This suggests that the superconducting mechanism of high  $T_c$  YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-δ</sub> is something like the BCS theory.

Since the high  $T_c$  ceramic superconductor, Ba-La-Cu-O system had been discovered by Bednorz and Muller [1] at 1986, many high  $T_c$  ceramic superconductors have been developed. These oxide superconductors have not only a high critical temperature but also extraordinary properties which are different from predictions of the BCS theory. Thereby, it is most exciting problem for a physicist to make clear a microscopic mechanism of the superconducting state. The mechanism intimately relates to the electronic states near the Fermi energy.

The tunneling spectroscopy is powerful probe in elucidating the mechanism, because it gives direct informations about the electronic states near the Fermi energy with high resolving power.

The tunnel junctions were fabricated by depositing SiO as a tunnel barrier and then Pb on YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-δ</sub> ceramic with  $T_c=88.5$  K (the off-set temperature in a temperature dependence characteristic of resistance). The V-dI/dV characteristics were traced at temperatures ranging over from 4.4 to 94.1 K as shown in Fig. 1. The scale of vertical axis is for the characteristic at 4.4 K. The V-dI/dV characteristic at 4.4 K has a valley centered at zero-bias and two peaks at  $\pm 5$  mV. These structures weaken with increasing temperature and disappear at temperature higher than 6.8 K and under the magnetic field higher than 1.2 kOe. Thereby, these structures come from a superconducting state of Pb.

The characteristic has two gentle curves ranging over from 10 mV (-10 mV) to

50 mV (-50 mV). These structures weaken with increasing temperature, and disappear higher than 80.5 K. Thereby, these structures come from the superconducting state of  $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ . Each characteristic is normalized with the one at 94.1 K, which is in the normal state, and then an energy gap  $\Delta$  at each temperature is obtained by using the Dynes' formula (2)

$$N_S(E)/N_N(0) = (E - i\Gamma) / \sqrt{(E - i\Gamma)^2 - \Delta^2}.$$

The temperature dependence of energy gap is shown in Fig. 2, where  $\Delta_0 = 15.5$  meV,  $T_c = 88.5$  K. Here, the value of energy gap at 4.4 K, 15.5 meV is assumed to be equal to a value at 0 K,  $\Delta_0$ . A solid line is the characteristic obtained by the BCS theory, and an open circle is the present value. As seen in Fig. 2, the present value agrees with the characteristic of BCS theory. Using  $\Delta_0 = 15.5$  meV and  $T_c = 88.5$  K, we obtain  $2\Delta_0/k_B T_c = 4.06$ . The value, 4.06 is near 4.3 for the strong coupling superconductor Pb. Recently, Tachiki and Takahashi theoretically showed that the BCS theory modified with a charge fluctuation gives a high  $T_c$  and a weak isotope effect. Our results seem to support Tachikis' theory.

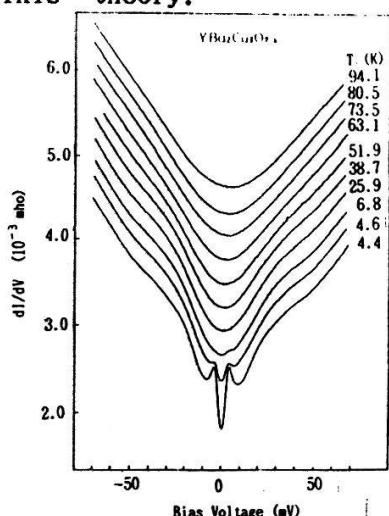


Fig. 1  $V$ - $dI/dV$  characteristics of  $\text{Pb-SiO-YBa}_2\text{Cu}_3\text{O}_{7-\delta}$  junction at temperatures ranging over from 4.4 to 94.1 K.

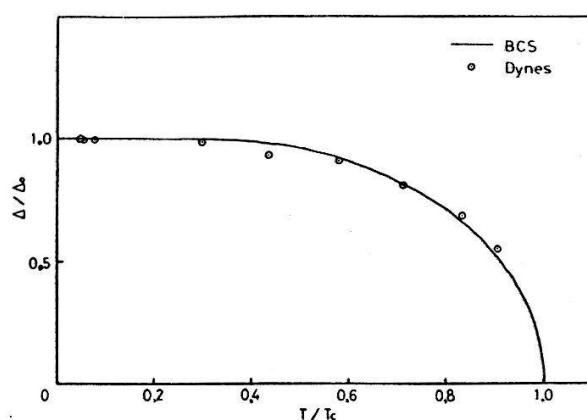


Fig. 2 Temperature dependence of energy gap for  $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ . A solid line is the BCS characteristic, and a circle the experimental value.

#### References

- (1) J. G. Bednorz and K. A. Muller: Z. Phys. B 64, 189(1986).
- (2) R. C. Dynes, J. P. Garno, G. B. Hertel, and T. P. Orlando: Phys. Rev. Lett. 53, 2437(1984).
- (3) M. Tachiki and S. Takahashi: Phys. Rev. B 39, 294(1989).