

High resolution photoemission investigation of phase transitions in 1T-TaS₂

Autor(en): **Dardel, B. / Grioni, M. / Malterre, D.**

Objekttyp: **Article**

Zeitschrift: **Helvetica Physica Acta**

Band (Jahr): **65 (1992)**

Heft 2-3

PDF erstellt am: **24.05.2024**

Persistenter Link: <https://doi.org/10.5169/seals-116494>

Nutzungsbedingungen

Die ETH-Bibliothek ist Anbieterin der digitalisierten Zeitschriften. Sie besitzt keine Urheberrechte an den Inhalten der Zeitschriften. Die Rechte liegen in der Regel bei den Herausgebern.

Die auf der Plattform e-periodica veröffentlichten Dokumente stehen für nicht-kommerzielle Zwecke in Lehre und Forschung sowie für die private Nutzung frei zur Verfügung. Einzelne Dateien oder Ausdrucke aus diesem Angebot können zusammen mit diesen Nutzungsbedingungen und den korrekten Herkunftsbezeichnungen weitergegeben werden.

Das Veröffentlichen von Bildern in Print- und Online-Publikationen ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. Die systematische Speicherung von Teilen des elektronischen Angebots auf anderen Servern bedarf ebenfalls des schriftlichen Einverständnisses der Rechteinhaber.

Haftungsausschluss

Alle Angaben erfolgen ohne Gewähr für Vollständigkeit oder Richtigkeit. Es wird keine Haftung übernommen für Schäden durch die Verwendung von Informationen aus diesem Online-Angebot oder durch das Fehlen von Informationen. Dies gilt auch für Inhalte Dritter, die über dieses Angebot zugänglich sind.

Ein Dienst der *ETH-Bibliothek*

ETH Zürich, Rämistrasse 101, 8092 Zürich, Schweiz, www.library.ethz.ch

High Resolution Photoemission Investigation of Phase Transitions in 1T-TaS₂.

B. Dardel, M. Grioni, D. Malterre, P. Weibel, and Y. Baer

Institut de Physique, Université de Neuchâtel, CH-2000 Neuchâtel, Switzerland

F. Lévy

Laboratoire de Physique Appliquée, EPFL, CH-1015 Lausanne, Switzerland

Abstract. Photoelectron spectroscopy with very high energy resolution reveals both dramatic and subtle changes in the electronic density of states of the quasi-2D material 1T-TaS₂, in coincidence with transitions between different charge density wave phases. Our results are consistent with the occurrence of a zero-gap Mott transition at ~185 K and of a subsequent Anderson localization in the pseudogap between the Hubbard subbands, and provide new insight into the unusual electronic properties of this material.

The layered compound 1T-TaS₂ exhibits unique physical properties which are related to, but are not fully explained by, the presence of a charge density wave (CDW) with a complex phase diagram. Especially the tenfold increase in the resistivity observed at the transition from a *quasi-commensurate* (QC) to a commensurate (C) CDW structure calls for an explanation other than the simple opening of a Peierls gap over portions of the Brillouin zone. Previous photoelectron spectroscopy (PES) studies have provided experimental support to a model predicting the occurrence of a Mott localization in coincidence with the QC-C transition. However, the values of the Mott-Hubbard gap (100-200 meV) estimated from PES data are incompatible with the results of transport measurements, which suggest a gap of the order of 1 meV.

We have addressed this controversial issue by a careful investigation of the temperature dependence of the electronic density of states (DOS) in the various CDW phases. The selected results presented here concern the QC-C transition. Our high resolution ($\Delta E \sim 15$ meV) PES spectra are very sensitive to small variations of the DOS occurring in the critical energy region, within a few $k_B T$ of the Fermi level (E_F), that determines the low-energy properties of the material. The dramatic effect that the QC-C transition produces on the DOS of 1T-TaS₂ is well illustrated by the valence band spectra of Fig. 1, which show that the sample evolves from a metallic to an apparently semiconducting state in less than 5 degrees. The prominent structure observed at a binding energy of 180 meV in the 186 K spectrum corresponds to the occupied Hubbard subband on the nonmetallic side of the Mott-Hubbard transition, and its binding energy is a measure of the on-site Coulomb correlation (U) in the Ta 5d band. Our results reveal the details of the growth and shift of this structure throughout the transition. We observe, at the transition temperature, a sharp

increase of the peak intensity, correlated with the resistivity jump, and with the sudden drop of the photoemission intensity at the Fermi level. This drop, reproduced in Fig.2, is a very direct evidence of the abrupt disappearance of most of the Fermi surface in coincidence with the QC-C transition. However, our results make clear that a finite electron density persists at E_F below the transition temperature and down to the experimental limit of 20 K. The separation of the Hubbard subbands is therefore incomplete and the Fermi level lies in a *pseudogap*. 1T-TaS₂ would therefore remain a metal, if localization due to disorder associated with the random distribution of impurities and defects, for which evidence exists from low-temperature resistivity data, did not occur in this pseudogap², probably around 180 K. Our results show that the relevant energy scale for the transport properties of this material is not defined by the binding energy of the Hubbard subband ($\sim U$) but by the difference between the Fermi energy and the mobility edge (which we estimate at ~ 5 meV). They also demonstrate that PES with state-of-the-art resolution can greatly contribute to our understanding of Fermi surface driven electronic instabilities.

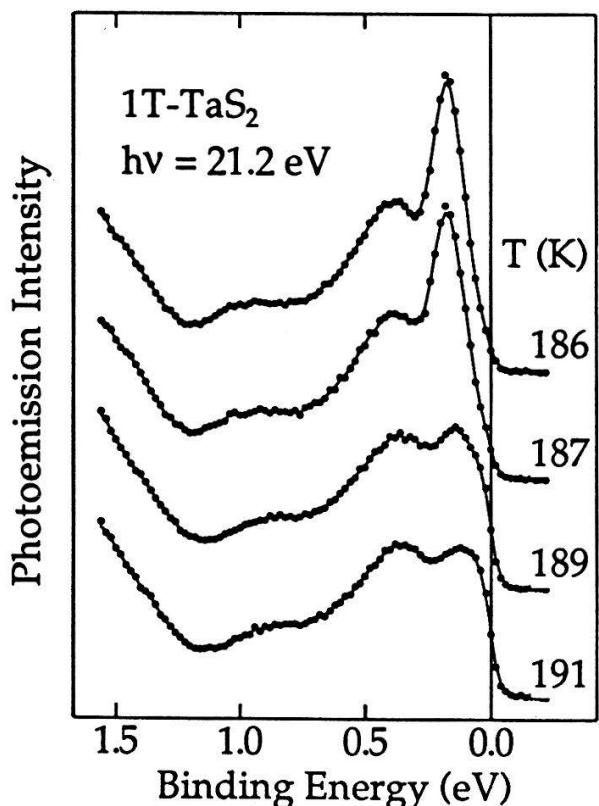


Fig.1. PES spectra of the valence band of 1T-TaS₂ through the QC-C CDW transition.

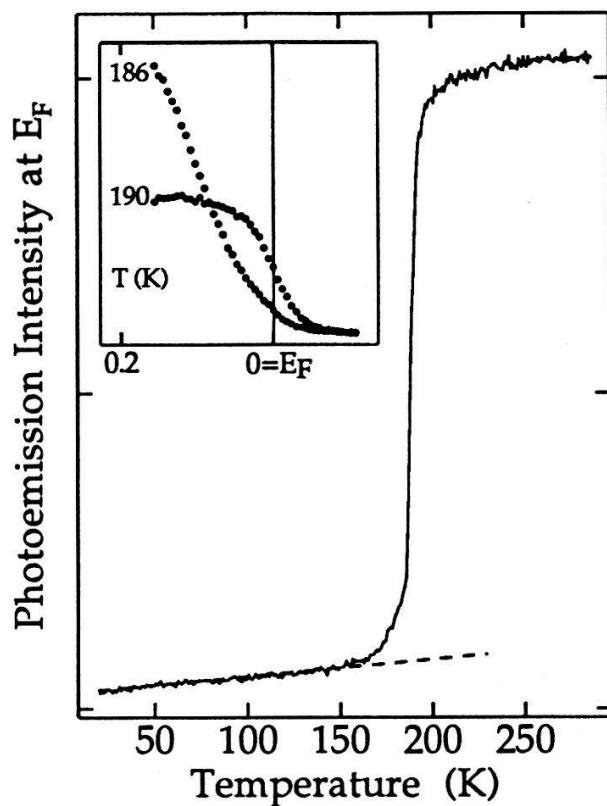


Fig.2. Temperature dependence of the PES intensity at E_F . **Inset:** Close-up of PES spectra near E_F .

References:

1. P. Fazekas and E. Tosatti, Phil. Mag. **B39**, 229 (1979).
2. D.J. Thouless, J. Phys. **37**, C4-349 (1976).