

Buckling curves of hot-rolled steel shapes with structural imperfections

Autor(en): **Mazzolani, Federico M.**

Objektyp: **Article**

Zeitschrift: **IABSE reports of the working commissions = Rapports des commissions de travail AIPC = IVBH Berichte der Arbeitskommissionen**

Band (Jahr): **23 (1975)**

PDF erstellt am: **10.08.2024**

Persistenter Link: <https://doi.org/10.5169/seals-19807>

Nutzungsbedingungen

Die ETH-Bibliothek ist Anbieterin der digitalisierten Zeitschriften. Sie besitzt keine Urheberrechte an den Inhalten der Zeitschriften. Die Rechte liegen in der Regel bei den Herausgebern.

Die auf der Plattform e-periodica veröffentlichten Dokumente stehen für nicht-kommerzielle Zwecke in Lehre und Forschung sowie für die private Nutzung frei zur Verfügung. Einzelne Dateien oder Ausdrucke aus diesem Angebot können zusammen mit diesen Nutzungsbedingungen und den korrekten Herkunftsbezeichnungen weitergegeben werden.

Das Veröffentlichen von Bildern in Print- und Online-Publikationen ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. Die systematische Speicherung von Teilen des elektronischen Angebots auf anderen Servern bedarf ebenfalls des schriftlichen Einverständnisses der Rechteinhaber.

Haftungsausschluss

Alle Angaben erfolgen ohne Gewähr für Vollständigkeit oder Richtigkeit. Es wird keine Haftung übernommen für Schäden durch die Verwendung von Informationen aus diesem Online-Angebot oder durch das Fehlen von Informationen. Dies gilt auch für Inhalte Dritter, die über dieses Angebot zugänglich sind.

BUCKLING CURVES OF HOT-ROLLED STEEL SHAPES
WITH STRUCTURAL IMPERFECTIONS

Federico M. Mazzolani
Professor of Civil Engineering
University of Naples
Italy

ABSTRACT

Theoretical and experimental researches directed to study the main buckling problems of metal members are carried out at the Istituto di Tecnica delle Costruzioni of the University of Naples (see bibliography 1,2,3,4,5,6,7,8).

The modern approach to the buckling problems requires to take into account structural imperfections, which characterize the actual bars and whose determination must be made in experimental way.

The principal results of experimental investigations on Italian hot-rolled steel shapes are here briefly summarized. Structural patterns of residual stresses have been obtained on the basis of such experimental results. Simulation calculations have provided the buckling curves for the examined profiles with structural imperfections. The simulation curves have been compared to the CECM-ECCS ones (9).

EXPERIMENTAL INVESTIGATION

The hot-rolled I shapes in structural steel Fe 42C, which have been examined, are:

IPE 200; HEA 100; HEB 100; HEM 100;
 HEA 200; HEB 200; HEM 200;
 HEA 300; HEB 300; HEM 300;

The following groups of tests have been made:

- a) Distribution on the cross section of the mechanical characteristics: yield point, ultimate strength, elongation, toughness, hardness; the principal scatters of the yield point distribution are shown in fig. 1.

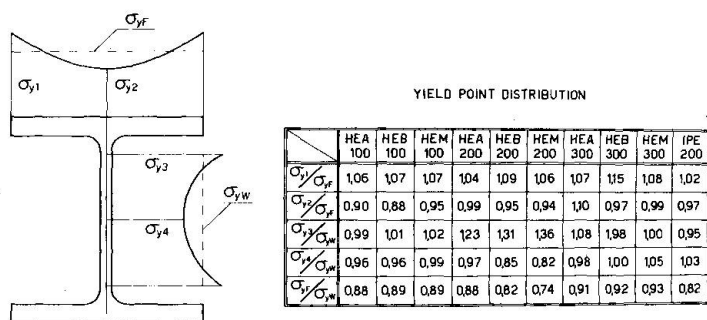


fig. 1

- b) Stub column tests; the lowering of the proportional limits appears from fig. 2

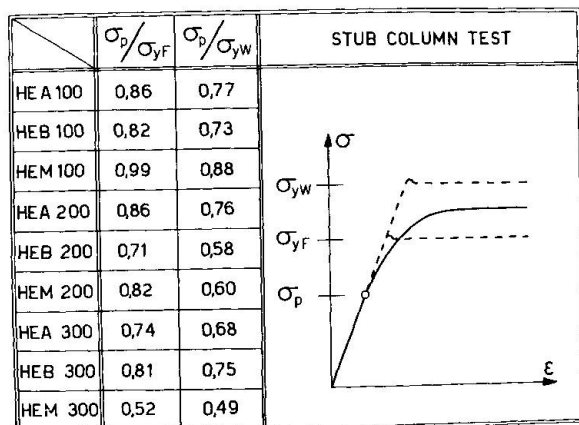


fig. 2

c) Evaluation of residual stresses by means of sectioning test; the interpretation of the experimental results leads to the pattern of fig. 3.

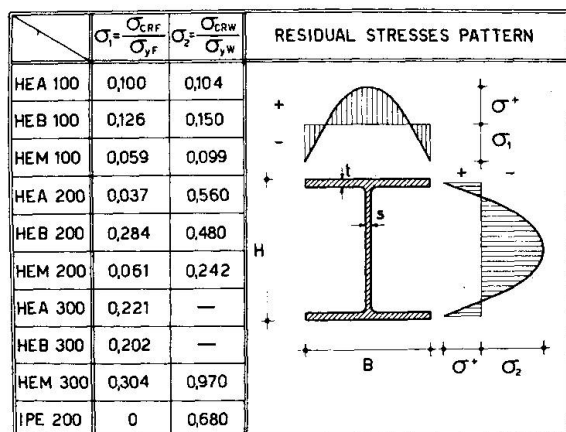


fig. 3

More details on the testing procedures and on the number of specimens are reported in (1), (7).

RESIDUAL STRESSES PATTERNS

The diagrams of residual stresses experimentally obtained have shown that the distributions are deeply influenced by the rotorizing procedure. Residual stresses in the flanges of the same bar, exhibit quite different distributions (fig. 4).

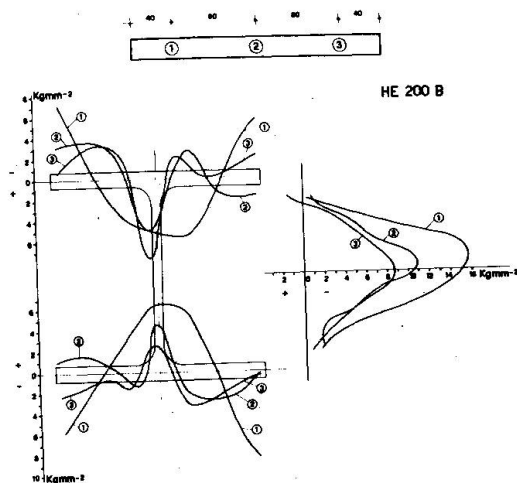


fig. 4

This fact makes impossible the statistical interpretation of the results and out of meaning the theoretical prediction of the thermal forming of residual stresses.

The collection of experimental data for a certain number of specimens makes possible the definition of bands which contain residual stresses for the examined shapes (fig. 5).

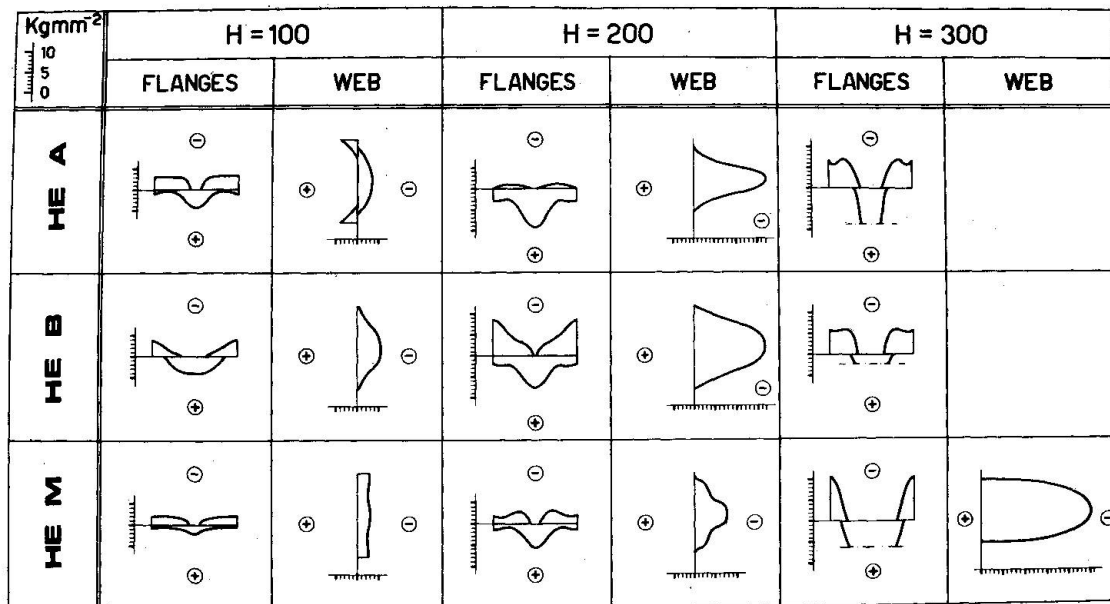


fig. 5

Starting from these data a structural pattern of residual stresses has been proposed, which utilizes the maximum compressive stresses at the edges of the flanges and at the center of the web. The condition that this pattern is in equilibrium leads to the residual stresses distributions shown in fig. 6 (1,5,6,7,3 cases). The cases 2 and 4 correspond to an average distribution and the case 3 considers the effect of the rotorizing straightening.

BUCKLING CURVES

The effect of the residual stresses distributions on the carrying capacity of simply compression columns has been examined by means of a simulation calculation. The residual stresses patterns and the average yield points used in the buckling calculations are shown in fig. 6.

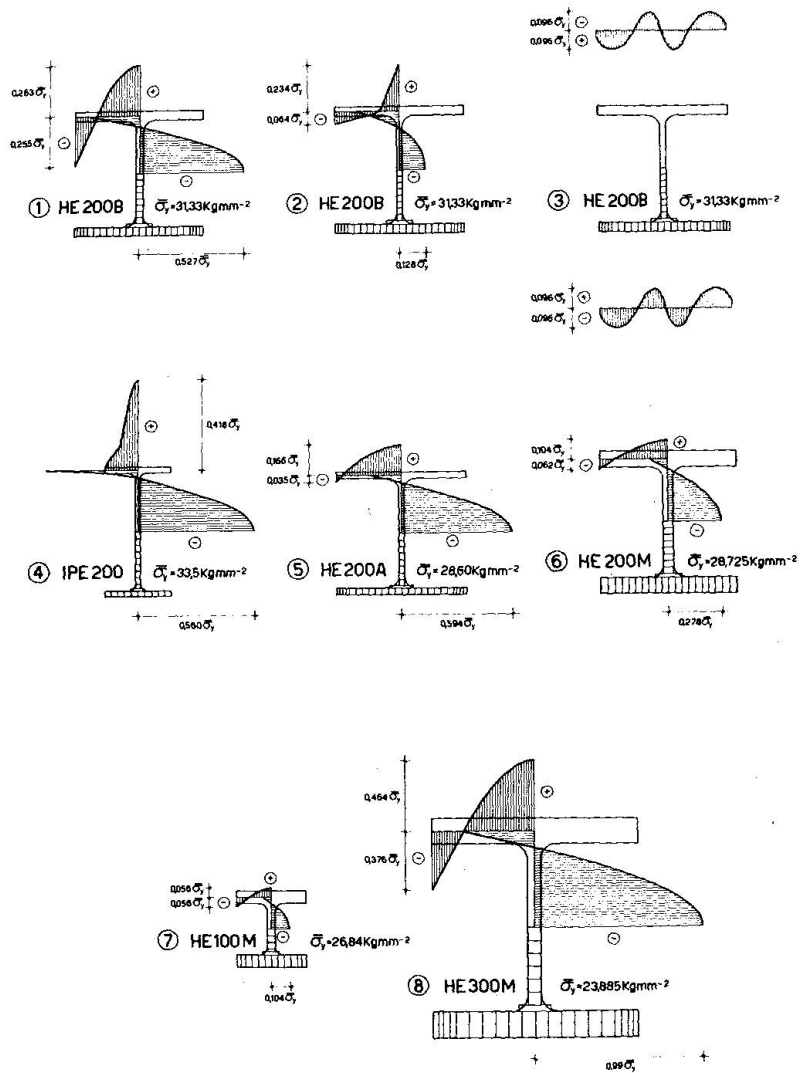


fig. 6

The numerical results have been obtained using the calculation program of the Centro Studi Costruzioni Metalliche (C.S.C.M.) of the Politecnico of Milan (10).

In order to compare the present results with the CECM-ECCS a,b,c curves the residual stresses distributions of fig. 6 have been considered together with the value $f/1 = 1/1000$ as geometrical imperfection, whereas the yield point distribution (fig. 1) has been neglected, using just the average values $\bar{\sigma}_y$ of fig. 6. The obtained dimensionless buckling curves, have^y been plotted in fig. 7,8,9, referring to the strong (max) and the weak (min) axes.

Fig. 7 shows the comparison among the residual stresses structural pattern (1), the average distribution (2) and the effect of rotorizing (3) in HEB 200 shapes.

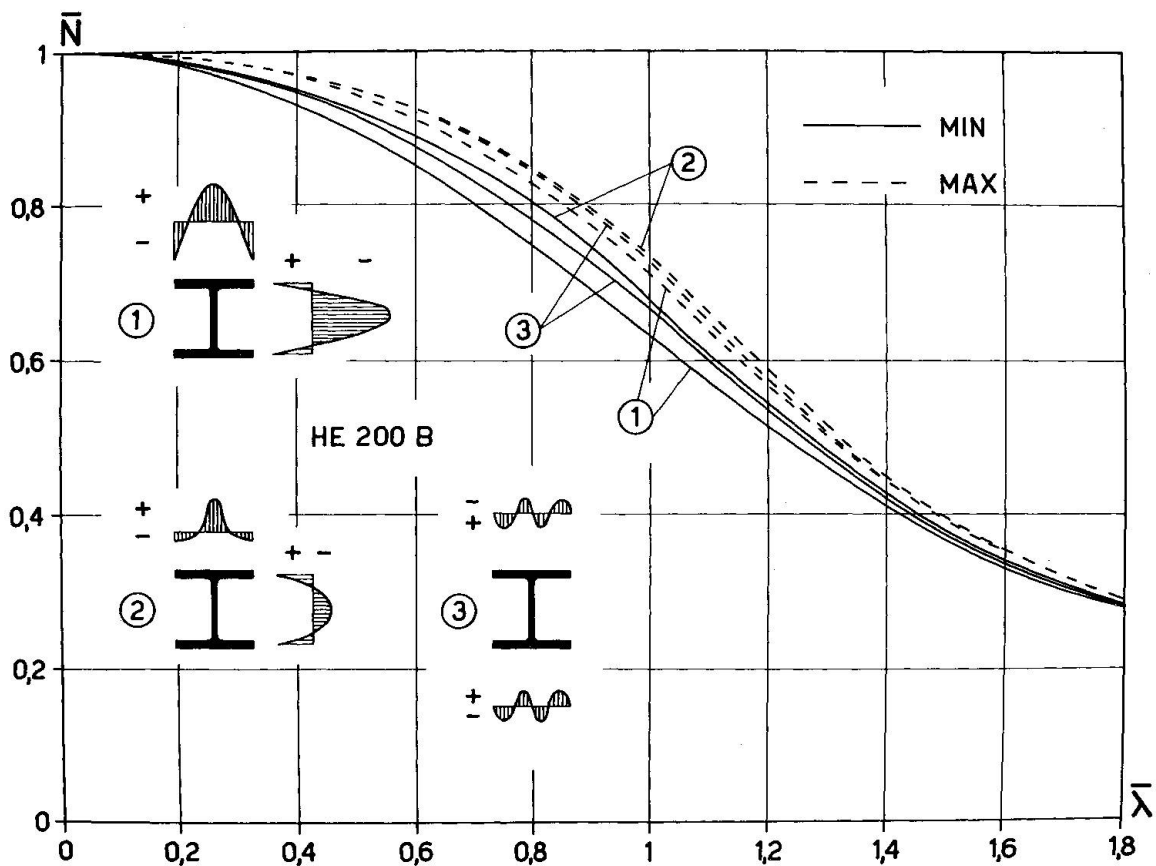


fig. 7

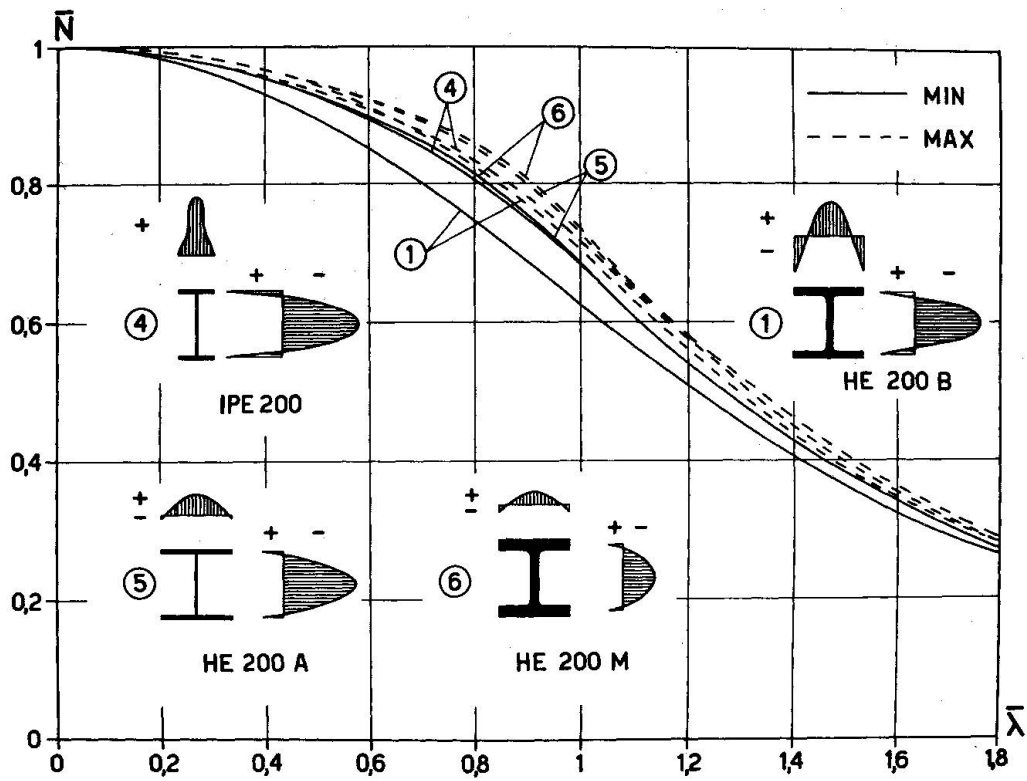


fig. 8

Different distributions of residual stresses on shapes with the same depth (HEA, HEB, HEM, IPE 200) lead to the buckling curves of fig. 8.

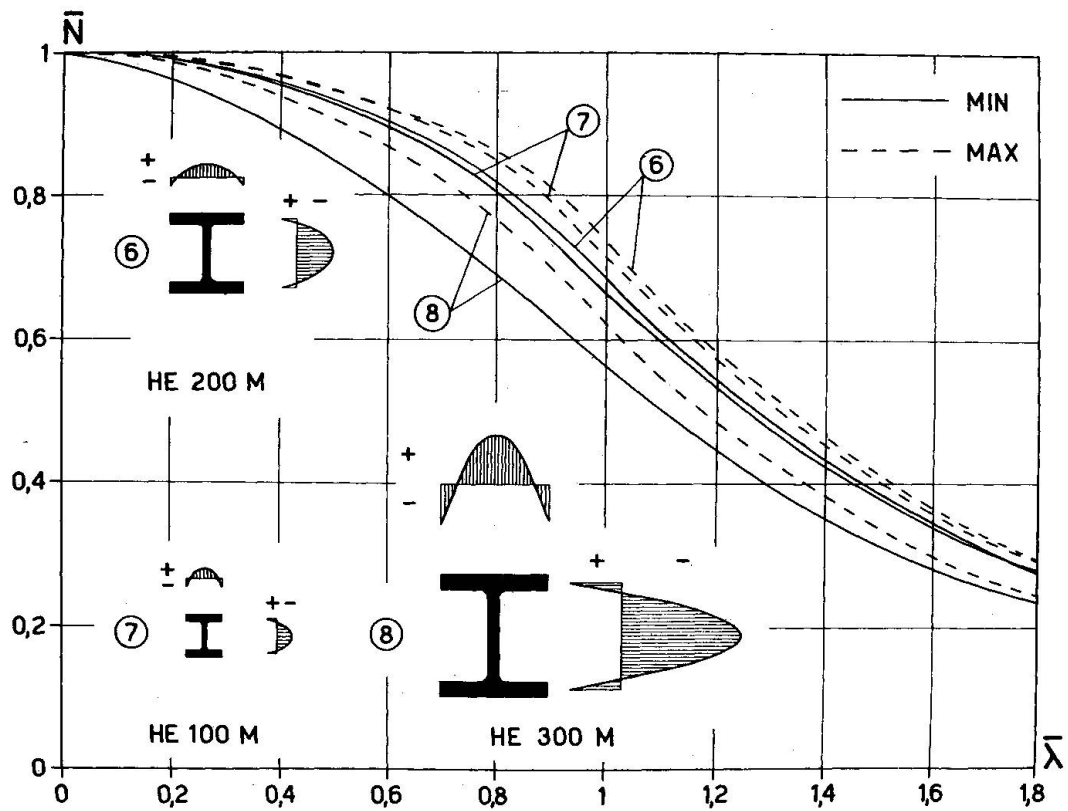


fig. 9

The distribution (1) of residual stresses in the HEB 200 represents always a lower bound for all the curves of fig. 7 and 3. The increase in depth for the same shape (HEM) makes the effect of residual stresses more important (fig. 9).

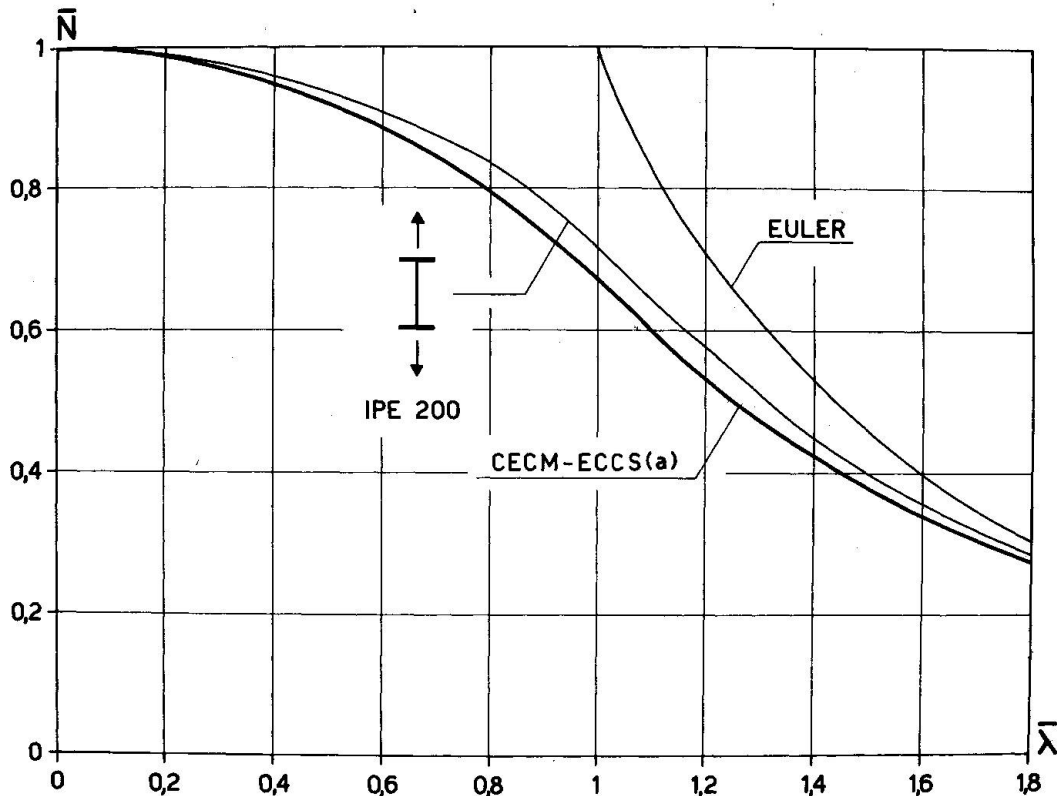


fig. 10

The obtained buckling curves have been plotted together with the CECM-ECCS a,b,c curves (fig. 10, 11, 12). The comparison between each calculated curves and the corresponding standard one shows that the CECM-ECCS curves are always more conservative than the simulation prediction based upon experimental residual stresses data. The difference may be explained, because only thermal residual stresses have been considered in the CECM-ECCS curves, without the favourable effect of rotorizing procedure, commonly used in the hot-rolled shapes manufacturing, which increases column strenght.

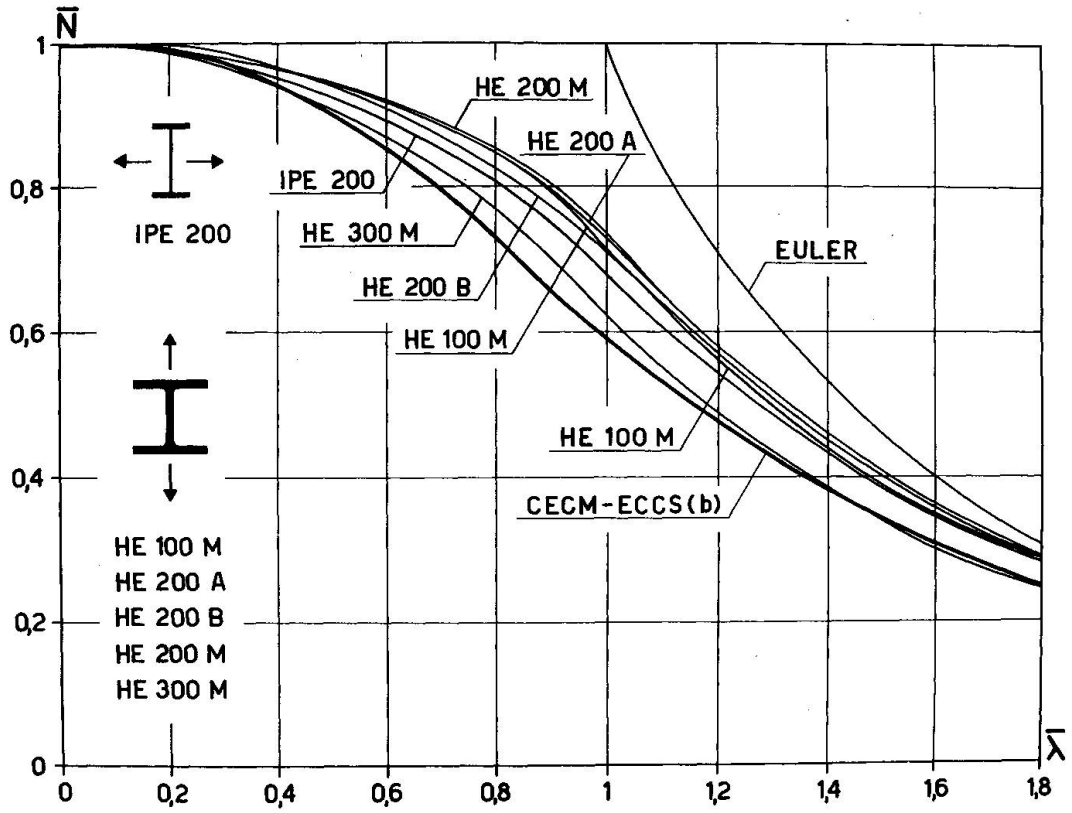


fig. 11

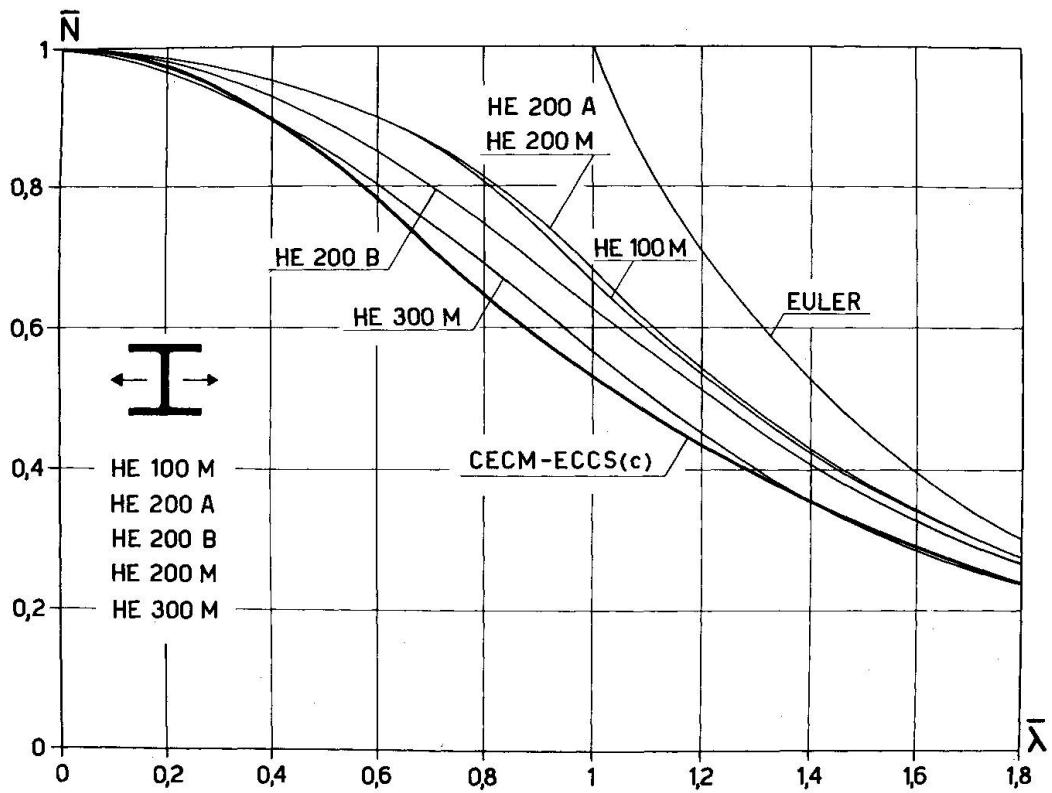


fig. 12

BIBLIOGRAPHY

- (1) M. COMO
F.M. MAZZOLANI "Ricerca teorico-sperimentale sullo svergolamento nel piano e fuori del piano dei profilati in presenza di tensioni residue" - Costruzioni Metalliche, n° 3, 1969.
- (2) F.M. MAZZOLANI "Plane, torsional and lateral buckling of I-metal shapes taking into account residual stresses" - Proceedings of the 4th Scientific Technological conference on "Metal Construction", Warsaw, 1970.
- (3) M. COMO
F.M. MAZZOLANI "Influence des contraintes rémanentes sur les problèmes fondamentaux de l'instabilité de forme" - Construction Métallique, n° 1, 1971.
- (4) F.M. MAZZOLANI "Il comportamento inelastico dei profili in alluminio saldati" - Costruzioni Metalliche, n° 5, 1971.
- (5) F.M. MAZZOLANI "Analisi sperimentale delle tensioni residue nei profilati metallici" - 1° Convegno Nazionale AIAS, Palermo 1972
- (6) F.M. MAZZOLANI "La caratterizzazione della legge σ - ϵ e l'instabilità delle colonne di alluminio" - Costruz. Metalliche n° 3, 72.
- (7) I. DADDI
F.M. MAZZOLANI "Determinazione sperimentale delle imperfezioni strutturali nei profilati di acciaio" - Costruz. Metalliche n° 5, 72.
- (8) C. FAELLA
F.M. MAZZOLANI "Instabilità flesso-torsionale inelastica di travi metalliche sotto carichi trasversali" - Costruzioni Metalliche, n° 6, 1972 (in the press).
- (9) H. BEER
G. SCHULZ "Bases théoriques des courbes européennes de flambement" - Construction Métallique, n° 3, 1970.
- (10) G. BALLIO
V. PETRINI
C. URBANO "Simulazione numerica del comportamento di elementi strutturali compressi per incrementi finiti del carico assiale" (In the press on Costruzioni Metalliche)