

Seismic retrofit of concrete columns using advanced composite materials

Autor(en): **Xiao, Yan**

Objekttyp: **Article**

Zeitschrift: **IABSE reports = Rapports AIPC = IVBH Berichte**

Band (Jahr): **999 (1997)**

PDF erstellt am: **08.08.2024**

Persistenter Link: <https://doi.org/10.5169/seals-1118>

Nutzungsbedingungen

Die ETH-Bibliothek ist Anbieterin der digitalisierten Zeitschriften. Sie besitzt keine Urheberrechte an den Inhalten der Zeitschriften. Die Rechte liegen in der Regel bei den Herausgebern.

Die auf der Plattform e-periodica veröffentlichten Dokumente stehen für nicht-kommerzielle Zwecke in Lehre und Forschung sowie für die private Nutzung frei zur Verfügung. Einzelne Dateien oder Ausdrucke aus diesem Angebot können zusammen mit diesen Nutzungsbedingungen und den korrekten Herkunftsbezeichnungen weitergegeben werden.

Das Veröffentlichen von Bildern in Print- und Online-Publikationen ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. Die systematische Speicherung von Teilen des elektronischen Angebots auf anderen Servern bedarf ebenfalls des schriftlichen Einverständnisses der Rechteinhaber.

Haftungsausschluss

Alle Angaben erfolgen ohne Gewähr für Vollständigkeit oder Richtigkeit. Es wird keine Haftung übernommen für Schäden durch die Verwendung von Informationen aus diesem Online-Angebot oder durch das Fehlen von Informationen. Dies gilt auch für Inhalte Dritter, die über dieses Angebot zugänglich sind.

Ein Dienst der *ETH-Bibliothek*

ETH Zürich, Rämistrasse 101, 8092 Zürich, Schweiz, www.library.ethz.ch

Seismic Retrofit of Concrete Columns Using Advanced Composite Materials

Yan XIAO

Asst. Professor of Civil Eng.
Univ. of Southern California
Los Angeles, CA, USA



Yan Xiao received his BS degree from Tianjin Univ., China, in 1982, and his MS and PhD degrees from Kyushu Univ., Japan, in 1986 and 1989, respectively. He has been on the faculty of the Univ. of Southern California since 1994.

Summary

In order to develop design guidelines for seismic retrofit of existing bridge columns using prefabricated composite jackets, six large scale bridge columns (Dia.=610mm) have been tested. Three columns with lap-spliced longitudinal bars were subjected to cyclic lateral forces in a single bending mode, while the other three columns were tested to simulate shear dominated bridge columns under cyclic loading with double bending. Test results demonstrated the superior retrofit effectiveness of the composite jackets.

Test of Shear Dominated Columns

The reinforcement details of shear test model columns are shown in Fig.1, and the test setup is shown in Fig.2. One column was tested in the "as built" condition and the other two models were tested after retrofit for the full column height using prefabricated composite jackets. Fig.3 shows the installation of the individual cylindrical prefabricated composite jacket. The "as built" column suffered a sudden shear failure during the loading cycle corresponding to a limited ductility factor of 3.0. The retrofitted columns developed significantly improved seismic performance characterized by large energy absorption capacities and stable hysteretic responses up to displacement ductility factors of 12 to 14, as shown in Fig.4.

Flexural Column Testing Program

Three circular columns with lap-spliced longitudinal reinforcement were tested under constant axial load and cyclic lateral forces in a single-curvature mode. One column was tested in the "as built" condition and others were tested after retrofit for the potential hinge region using prefabricated composite jackets. The "as built" model column failed without developing its predicted flexural capacity due to severe deterioration in the lap-spliced longitudinal bars. The two retrofitted columns, one retrofitted with 5-layer individual prefabricated composite jackets and the other with 5-layer continuous jackets developed significantly improved seismic

performance demonstrating the excellent effectiveness of prefabricated composite jackets for flexural retrofit. The retrofitted columns exhibited stable behaviors until a displacement ductility factor of 8.0. Although a gradual degradation of load carrying capacity was observed during loading cycles corresponding to large deformation, the two retrofitted columns were able to develop an ultimate displacement ductility factor of 10.0.

Concluding Remarks

Current study provides methods for seismic retrofit and repair of reinforced concrete columns. Prefabricated composite jacketing can also be considered for repair and protection of column supported structures from environmental damage and exposure. Studies will be initiated in near future to address the applications of prefabricated composite jacketing in: columns subjected to freeze/thaw and deicing salt corrosion in snow belt states and countries; structures deteriorated due to water absorption of porous concrete; harbor wharf and pilings; power/telephone poles; structures damaged by fires, etc.

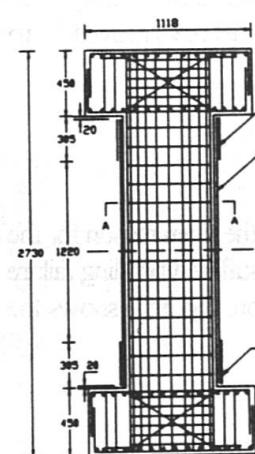


Fig.1. Shear Test Column Details

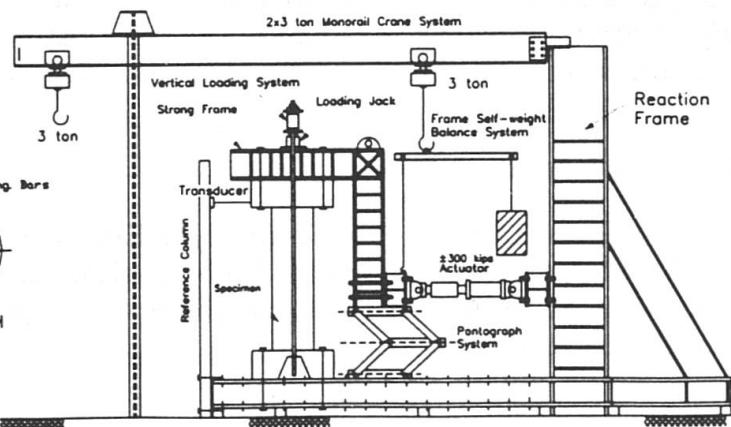


Fig.2. Shear Test Setup

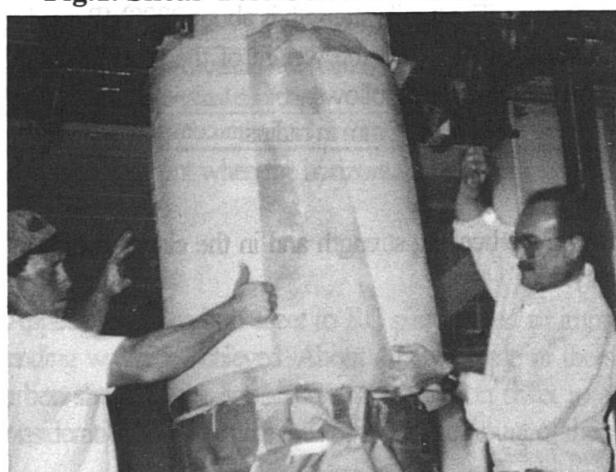


Fig.3. Installation of Prefabricated Composite Jackets

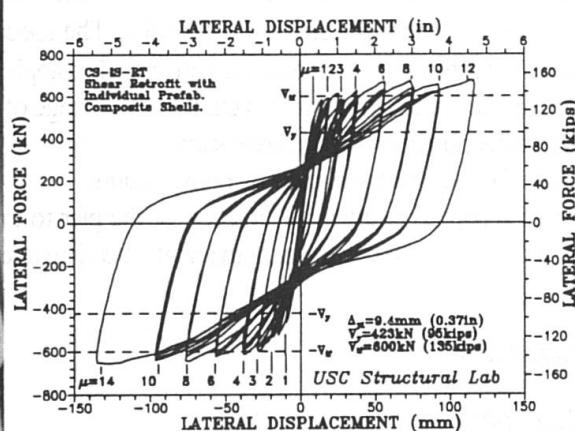


Fig.4. Hysteretic Response of Shear Column with Individual Shell Retrofit