

**Zeitschrift:** Schweizerische mineralogische und petrographische Mitteilungen =  
Bulletin suisse de minéralogie et pétrographie

**Band:** 71 (1991)

**Heft:** 1

**Artikel:** Preparation and cell refinement of mica microsamples

**Autor:** Stern, W.B.

**DOI:** <https://doi.org/10.5169/seals-54353>

### **Nutzungsbedingungen**

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. [Siehe Rechtliche Hinweise.](#)

### **Conditions d'utilisation**

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. [Voir Informations légales.](#)

### **Terms of use**

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. [See Legal notice.](#)

**Download PDF:** 13.10.2024

**ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>**

Frau Prof. Dr. Emilie Jäger gewidmet

## Preparation and cell refinement of mica microsamples

by W. B. Stern<sup>1</sup>

### Abstract

Least squares refinement of X-ray powder diffractograms of mica microsamples is possible when preferred orientation is minimized electrostatically. Their relative 1-sigma errors for a, b, c and cell volume are 0.06, 0.04, 0.02 and 0.05% respectively. The correlation of a and b parameters is within the statistical error of data, but a, b versus c scatter far more. When literature cell parameters of pure end members muscovite-phengite-paragonite are combined in a triangular grid and used for a diffraction analysis of white 2M1-mica, the results obtained correspond trendwise only with chemical analyses performed on the same micas. One may conclude that even qualitative chemical analysis on microsamples (e.g. by energy-dispersive X-ray fluorescence) enables more reliable results than high-quality diffraction data. Though cell parameters a and b of white mica are certainly linked with "phengite"-, and c with "paragonite"-content, the interdependence seems to be more complex than expected from literature.

*Keywords:* 2M1-mica, cell refinement, X-ray diffraction, microsample, chemical composition.

### Zusammenfassung

Zellverfeinerungen pulverdiffraktometrischer Aufnahmen von Mikroproben sind im Falle von Hellglimmer möglich, wenn Orientierungseffekte elektrostatisch reduziert werden. Typische 1-sigma-Relativfehler für a, b, c und Zellvolumen sind 0,06, 0,04, 0,02 und 0,05% für 2M1-Hellglimmer, von denen 53 unterschiedlicher Herkunft diffraktometrisch und röntgenfluoreszenzanalytisch untersucht worden sind. Werden aus der Literatur die b- und c-Zellparameter von Muskowit, Phengit und Paragonit in einem Dreiecksdiagramm kombiniert und zur diffraktometrischen «Analyse» von Hellglimmer verwendet, so zeigen die gefundenen Werte zwar eine ungefähre Korrelation mit den an denselben Proben erhobenen chemischen Daten; von einem quantitativen Zusammenhang kann aber – trotz der kleinen Relativfehler (XRD) – keine Rede sein. Offensichtlich sind die Beziehungen zwischen Gittergrösse und Chemismus komplexer, als z.B. durch die Bezeichnung «Phengit» zum Ausdruck kommt, bei dem Mg, Fe<sup>2+</sup> und Fe<sup>3+</sup> einen unterschiedlichen und wohl auch gegenläufigen Einfluss auf die a- und b-Parameter haben können.

### Introduction

Lattice dimensions of crystals are essential parameters, but not easy to determine on low-symmetry flaky minerals like mica. When chemical data, based on bulk mineralogical (powdered) specimens are correlated with lattice parameters, the latter should be determined on powdered samples as well (not on single crystals), preferably on the same specimen, from which chemical information was obtained.

A recently developed preparation method for diffraction and chemical investigation on micro-

samples (HANDSCHIN, STERN, 1990) was tested by studying dioctahedral micas from schists, gneisses, granites and pegmatites of various origin.

### Procedures and results

#### X-RAY DIFFRACTION (XRD)

When microsamples have to be investigated by X-ray diffraction or fluorescence, the size of sample surface is important in order to get statistically relevant signals. Thus, 30 mg of powdered mica

<sup>1</sup> Mineralogisch-Petrographisches Institut der Universität, Bernoullistrasse 30, CH-4051 Basel.

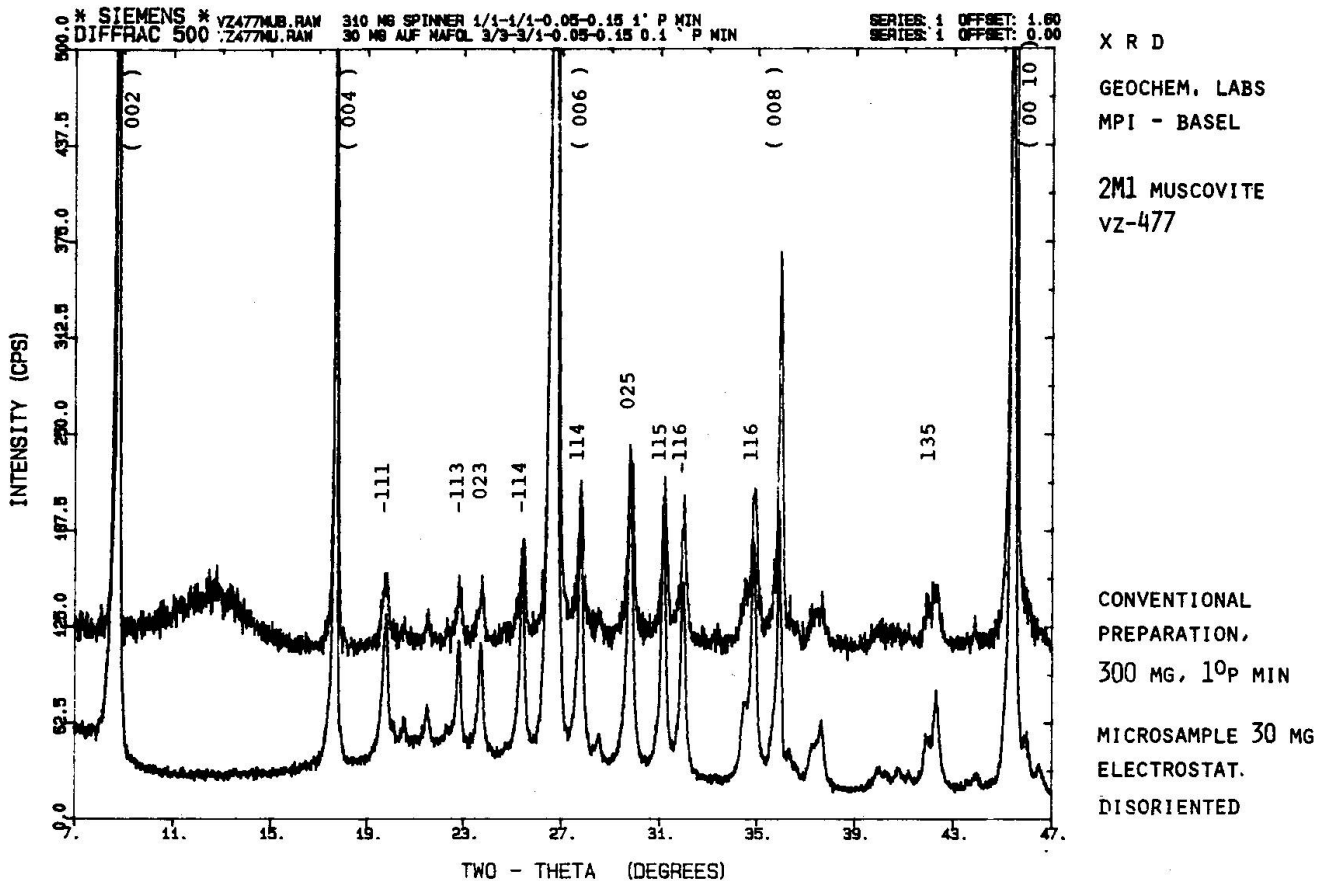


Fig. 1 X-ray diffraction pattern of powdered 2M1 – muscovite (Vz 477): Comparison between conventional preparation (300 mg in sample cup) and electrostatically disoriented microspecimen (30 mg) on stretched foil. Non-basal reflections of the disoriented microsample display double net intensities.

(10 mg would do as well for diffraction work) were distributed evenly on a stretched foil of 40 mm diameter, and fixed to it with 0.25 ml Griltex solution. In order to minimize preferred orientation, the mica flakes were disordered electrostatically by moving a plexiglass rod close to the surface of the drying mica / Griltex film.

In contrast to conventional mounting (e.g. 300 mg powdered mica in a sample cup or smear slides) not only basal spacings (00l) are prominent, but also random hkl-reflections (Fig. 1). Since least squares cell refinement (APPLEMAN, EVANS, 1973) of a monoclinic structure needs around 20 linearly independent strong reflections, it is evident that only disoriented samples can be used. Even these diffraction patterns may lead to plausible, but nevertheless erroneous cell parameters (STERN, 1987), when statistics of signal/peak ratios are not appropriate.

In order to combine suitable resolution and signal statistics, the samples were run with an angular goniometer speed of 0.1 degrees  $2\theta$  only (around 12 hours per exposure); least squares refinements were performed on-line after data reduction, the results transferred to a Lotus worksheet (reg. trade

name LOTUS 1-2-3, version 3.0), (Fig. 2, Tab. 1). The statistical average errors are  $\pm 0.003 \text{ \AA}$  for a, 0.004 for b and c, and  $0.4 \text{ \AA}^3$  for the cell volume respectively.

The correlation of a and b parameters is fair and corresponds to literature data, e.g. from BORG and SMITH, 1969 (Fig. 2).

#### X-RAY FLUORESCENCE (XFA)

During the past few years a large amount of micas and "coexisting" mica pairs was re-examined with improved wavelength- and energy-dispersive X-ray fluorescence methods (WD-XFA, ED-XFA) for main constituents and trace elements, part of these unpublished data were used here to correlate them with XRD data.

Quantitative WD-XFA is still (STERN, 1979) executed on fused minerals for main element analysis, and on pressed powders for trace element analysis, both routines taking advantage of fully automated procedures optimized for intensity (matrix-) corrections. All data were automatically transferred to a Lotus worksheet file for further processing and graphical display.

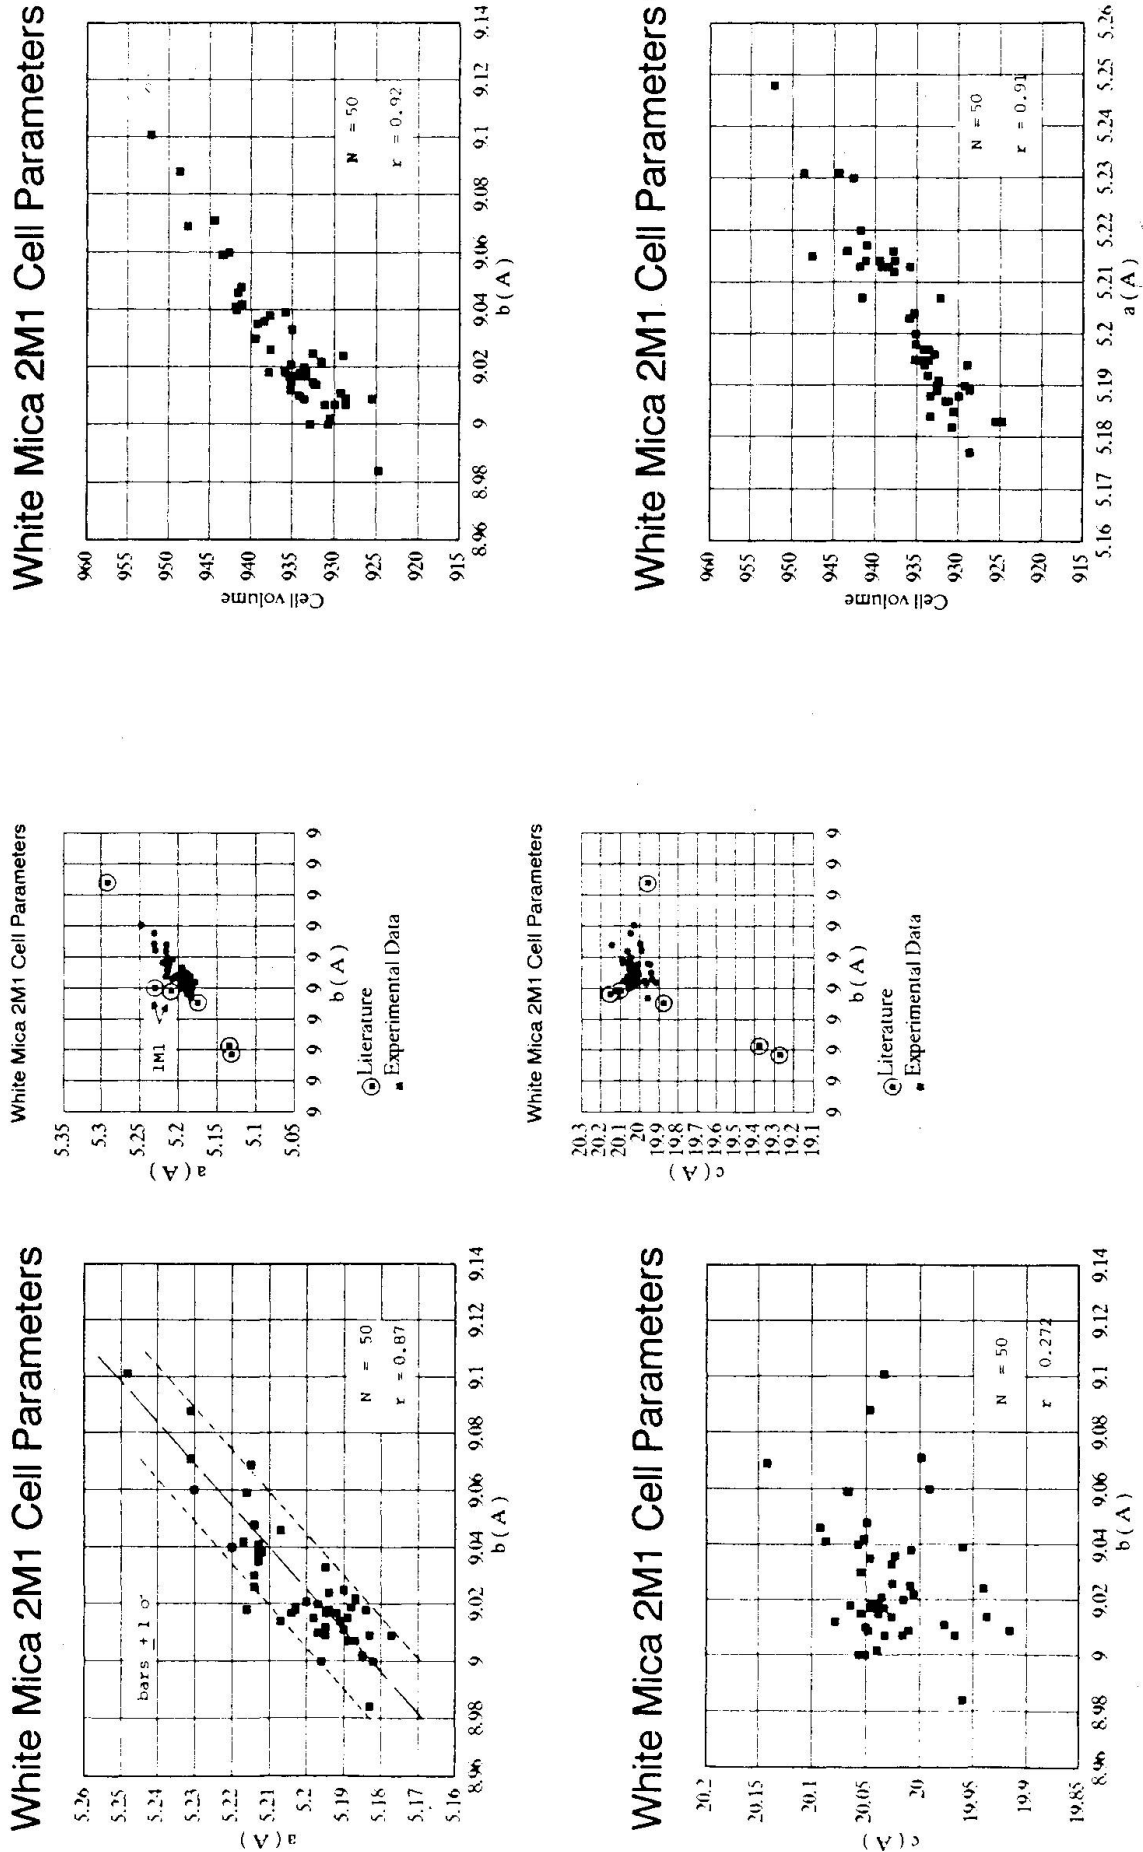


Fig. 2 Experimental X-ray powder diffraction data, and values from literature (for key see Fig. 4). Correlation of lattice parameters a versus b, and a, b versus cell volume are highly significant, in contrast to b versus c. Position and slope of the a versus b regression line corresponds well with data from literature (small inset). Note that 1M polytypes tend to plot outside the a/b correlational field of 2M1 white mica.

Tab. 1a Data White Mica (XRD) and selected chemical data (XFA).

2M1 Sample	Origin	Host Grp	a (Å)	b (Å)	c (Å)	error	beta	volume	Std. err.	log-ratios ex-XFA K/K <sub>0</sub> Ba Si/Al Al/Fe. K/Rb HK=Oxide	ED-XFA W0-XFA Fe203t	Specimen no.	Calculated (XFA) Pheng Si/Al Na/Ra+ %	Musc %									
Ad41b	Bernardino	Sh	5.213	0.002	9.039	0.003	19.960	0.002	0.3	0.012	0.051	0.236	0.610	*	0.14	3.88	4.10	40.1	59.9				
Cal26	Calanca	Sh	5.200	0.002	9.021	0.002	20.035	0.001	95.8	935.8	0.3	0.012	-0.029	0.182	0.820	2.600	0.41	3.21	2.57	XV7361	27.0	4.6	68.5
Gl111	Bernardino	Gn	5.231	0.004	9.071	0.005	19.999	0.003	95.8	935.1	0.7	0.016	-0.009	0.255	0.446	2.120	0.19	7.15	7.08	XV7658	44.7	0.0	55.3
Ha225	Laengtal	Sh	5.190	0.003	9.011	0.004	19.977	0.006	95.9	929.2	0.5	0.019	-0.133	0.373	0.660	2.440	-0.02	2.39	2.69	XV7634	73.4	13.1	13.6
KAW0165	Eisten	Gn	5.230	0.003	9.060	0.004	19.991	0.003	95.7	942.6	0.5	0.015	-0.003	0.285	0.360	2.310	0.46	7.14	8.58	XV7642	52.0	0.7	47.3
Vals1	Vals	Gn	5.194	0.002	9.024	0.003	19.940	0.003	95.8	928.9	0.3	0.015	-0.046	0.269	*	0.15	4.50	4.10	47.1	52.9			
Bedr107a	Breditto	Gn	5.207	0.003	9.014	0.008	19.937	0.001	95.0	932.1	0.7	0.011	-0.013	0.247	0.580	2.520	0.36	4.65	5.29	XV7537	42.8	0.7	56.6
Blen49	Blenio	Sh	5.217	0.005	9.042	0.009	20.052	0.004	95.9	941.0	0.9	0.022	-0.010	0.138	0.951	2.554	0.34	2.51	2.66	XV7357	16.3	83.7	16.3
Cl22d	Levent	Gn	5.185	0.003	8.992	0.006	19.887	0.030	95.6	922.7	0.6	0.016	-0.076	0.093	1.410	2.590	0.05	1.61	0.82	XV7638	5.3	14.9	79.7
Gl104	Chiavenna	G	5.182	0.004	9.000	0.005	20.056	0.002	95.7	930.7	0.6	0.022	-0.010	0.128	1.180	2.210	0.46	1.88	1.79	XV7523	13.9	1.1	85.0
Hal99	Tosafall	Gn	5.213	0.001	9.036	0.003	20.023	0.001	95.7	938.4	0.4	0.015	-0.009	0.190	0.690	2.270	0.35	4.45	4.50	XV7345	28.9	7.8	63.3
KAW0160	Lebedun	Gn	5.212	0.002	9.038	0.004	20.008	0.002	95.8	937.7	0.4	0.017	-0.006	0.192	0.620	2.300	0.48	5.40	5.89	XV7615	29.4	0.7	69.9
KAW0207	Brintal	Gn	5.248	0.002	9.101	0.002	20.033	0.004	95.8	952.1	0.4	0.022	-0.008	0.275	0.420	1.960	0.46	7.19	7.68	XV7473	49.6	0.4	50.0
Hul132	Antignorio	Sh	5.189	0.003	9.007	0.004	19.967	0.001	95.7	928.6	0.5	0.012	-0.043	0.121	0.860	2.610	0.56	3.68	3.80	XV7549	12.2	7.6	80.2
HuSt900	Bavona	Gn	5.214	0.004	9.026	0.005	20.025	0.002	95.8	937.6	0.6	0.018	-0.022	0.233	1.036	2.310	0.36	2.76	4.40	XV7506	39.4	4.1	56.6
KAW0082	Croppo	Gn	5.214	0.003	9.048	0.011	20.049	0.002	95.8	941.1	0.9	0.018	-0.007	0.144	0.920	2.310	0.42	3.01	3.02	XV7646	17.7	1.6	80.7
KAW0083	Beura	Gn	5.216	0.004	9.018	0.005	20.040	0.001	95.8	937.8	0.5	0.016	-0.004	0.171	0.810	2.390	0.38	3.00	3.66	XV7630	24.3	0.3	75.4
Vz691	Verzasca	Sh	5.183	0.001	8.984	0.002	19.960	0.002	95.7	924.7	0.3	0.017	-0.410	0.110	1.175	2.660	-0.31	0.93	0.84	XV7674	9.5	3.8	86.7
Gl110	Prato	P	5.203	0.003	9.019	0.003	20.044	0.001	95.8	935.9	0.3	0.008	-0.018	0.142	0.804	2.464	0.67	4.07	4.45	XV7553	17.3	2.3	80.5
Vz297	Lavertezzo	P	5.195	0.001	9.009	0.002	20.048	0.001	95.8	933.5	0.2	0.016	-0.015	0.155	1.010	2.380	0.41	2.32	2.44	XV7506	20.4	2.3	77.3
Vz477	Odro	P	5.216	0.003	9.059	0.002	20.066	0.004	95.8	943.3	0.5	0.019	-0.008	0.159	0.700	1.760	0.87	6.56	6.20	XV7375	21.4	1.5	77.1
Vz501	Lavertezzo	P	5.187	0.001	9.007	0.001	20.032	0.001	95.8	931.1	0.2	0.011	-0.025	0.142	0.930	2.240	0.48	2.22	2.90	XV7631	17.3	5.5	77.2
WS62a	Morobbia	P	5.198	0.004	9.015	0.004	20.055	0.003	95.8	935.1	0.5	0.020	-0.014	0.126	1.156	2.640	0.37	1.79	1.79	XV7584	13.3	2.2	84.5
WS72b	Novate	G	5.185	0.002	9.002	0.003	20.039	0.002	95.7	930.5	0.3	0.014	-0.009	0.115	1.030	2.360	0.61	1.80	2.70	XV7603	10.7	1.2	88.1
81.200	Irkutsk	P	5.213	0.004	9.035	0.006	20.046	0.002	95.8	939.2	0.5	0.019	-0.032	0.117	0.950	2.370	0.17	1.83	2.35	XV4994	11.2	2.5	86.4
83.330	Rustum	P	5.190	0.003	9.025	0.002	20.009	0.002	95.8	932.5	0.4	0.015	-0.020	0.213	0.432	2.120	0.64	4.66	8.52	XV6367	34.5	4.0	61.5
86.321	Kali-b	P	5.196	0.003	9.000	0.003	20.051	0.001	95.8	932.8	0.4	0.011	-0.036	0.107	1.126	2.340	0.36	1.28	1.94	XV6290	8.7	6.9	84.3
86.323	Sharda	P	5.195	0.004	9.033	0.004	20.026	0.002	95.7	935.0	0.5	0.017	-0.030	0.149	0.782	1.530	0.63	2.68	4.11	XV6321	19.0	5.7	75.4
86.326	Badani	P	5.191	0.002	9.014	0.003	20.026	0.001	95.7	932.3	0.3	0.011	-0.021	0.117	0.985	1.629	0.49	2.56	2.81	XV6319	11.2	3.4	85.4
88.003gr	Morocco	P	5.184	0.002	9.018	0.003	20.064	0.003	95.8	933.3	0.4	0.017	-0.031	0.108	1.185	1.610	0.54	1.67	2.14	XV6542	9.0	5.9	85.1
88.005ru	Morocco	P	5.194	0.004	9.018	0.004	20.038	0.003	95.8	934.0	0.6	0.019	-0.031	0.128	0.936	1.840	0.41	2.88	3.35	XV6543	13.9	6.3	79.9
88.008	Argentina	P	5.204	0.002	9.017	0.001	20.033	0.002	95.8	935.3	0.3	0.015	-0.029	0.149	0.681	2.370	0.62	3.82	5.50	XV6544	19.0	5.7	75.4
88.010	Shivsh	P	5.195	0.003	9.017	0.003	20.046	0.004	95.8	934.3	0.3	0.011	-0.033	0.099	1.172	1.150	0.62	1.75	1.70	XV7084	6.8	1.7	91.5
89.001	Sitarama	P	5.197	0.001	9.020	0.003	20.015	0.002	95.8	933.5	0.2	0.012	-0.040	0.117	1.050	2.620	0.22	1.82	2.02	XV7265	11.2	4.4	84.4
89.003	Menakshi	P	5.187	0.002	9.022	0.004	20.005	0.002	95.8	931.5	0.4	0.017	-0.041	0.131	0.860	2.550	0.43	2.30	3.51	XV7267	14.6	2.6	82.9
89.005gr	PVSR-India	P	5.231	0.002	9.088	0.003	20.046	0.006	95.8	948.6	0.4	0.018	-0.008	0.174	0.532	2.160	0.79	6.47	7.90	XV7269	25.0	3.2	71.8
89.006	Vandana	P	5.195	0.004	9.012	0.005	20.078	0.004	95.8	935.2	0.6	0.019	-0.015	0.101	1.230	2.310	0.62	1.64	1.78	XV7271	7.3	3.0	89.7
90.009	Tucuman	P	5.216	0.003	9.059	0.011	20.067	0.004	95.8	943.4	0.9	0.028	-0.013	0.111	0.949	2.444	0.47	2.07	3.10	XV7703	9.7	4.3	86.0
90.010	Argentina	P	5.220	0.002	9.040	0.004	20.057	0.002	95.8	941.7	0.3	0.019	-0.010	0.075	0.982	2.465	0.50	1.80	3.13	XV7705	1.0	2.3	96.8
90.011	Zimbabwe	P	5.214	0.002	9.030	0.003	20.055	0.002	95.8	939.4	0.3	0.017	-0.010	0.064	1.059	2.137	0.87	2.81	3.10	XV7707	0.0	0.0	0.0
89.009	Tanzania	P	5.215	0.004	9.069	0.014	20.141	0.009	95.9	947.6	1.6	0.038	-0.023	0.118	0.996	2.620	0.20	1.30	2.23	XV7085	11.4	2.2	86.4
Shilling	Sudan	P	5.177	0.003	9.009	0.006	20.010	0.003	95.7	928.6	0.7	0.019	-0.027	0.149	0.861	2.320	0.38	2.14	3.00	XV6532	19.0	5.1	76.0
086.010	Malaysia	G	5.197	0.002	9.010	0.005	20.050	0.005	95.8	934.1	0.6	0.020	-0.035	0.228	0.839	1.762	0.52	3.32	XV7305	38.2	4.5	57.3	
094.004	Malaysia	G	5.213	0.002	9.041	0.003	20.087	0.005	95.8	941.8	0.3	0.015	-0.017	0.133	0.910	1.650	0.77	5.19	3.64	XV7307	15.1	3.1	81.8
094.008	Malaysia	G	5.207	0.001	9.046	0.006	20.092	0.004	95.8	941.5	0.3	0.020	-0.010	0.150	0.900	1.660	0.88	2.47	3.47	XV7309	19.2	1.4	79.4
094.009	Malaysia	G	5.188	0.001	9.019	0.005	20.045	0.003	95.7	933.3	0.5	0.023	-0.017	0.150	0.990	1.670	0.61	2.41	2.68	XV7311	19.2	2.1	78.7
094.010	Malaysia	G	5.203	0.002	9.018	0.003	20.044	0.001	95.8	935.8	0.3	0.013	-0.013	0.144	0.960	1.740	0.55	4.09	2.91	XV7313	17.7	2.1	80.2
094.014	Malaysia	G	5.189	0.001	9.015	0.003	20.038	0.004	95.8	932.5	0.1	0.014	-0.013	0.152	0.840	1.720	0.63	4.11	3.95	XV7317	19.7	1.4	79.0
094.015	Malaysia	G	5.192	0.002	9.017	0.003	20.045	0.003	95.8	933.6	0.4	0.013	-0.006	0.159	0.880	1.790	0.58	2.61	3.37	XV7317	21.4	0.8	77.8
103.001	Malaysia	G	5.188	0.003	9.007	0.007	20.016	0.011	95.8	929.9	0.8	0.033	-0.019	0.232	0.900	1.740	0.63	3.67	3.11	XV7321	39.1	2.9	58.0
Polytypes other than 2M1																							
KAW0041	Nalps	P	8.878	0.010	5.249	0.003	20.420	0.003	99.8	937.8	0.8	0.021	-0.007	0.134	1.110	2.450	0.64	1.98	2.30	XV7343	1.1	98.9	1.1
Vz690	Verzasca	Sh	5.169	0.005	8.991	0.003	10.145	0.003	97.9	467.0	0.5	0.007	-0.068	0.167	1.098	2.570	0.64	0.83		IX962	14.4	85.6	14.4

Tab. 1b Data White Mica (XRD) and selected chemical data (XFA).

Reproducibility test on one microsample ( 30 mg Rustum 83.330 )		Reflections rejected		Remarks													
		Iter	Reflections used	Std.err.	Remarks												
RUSTUM	A. Pradesh	P	5	5.190	0.003	9.025	0.002	20.009	0.002	95.79	932.5	0.4	4	20	0.015	sample position normal, 0.1'p min	
RUSTUM2	A. Pradesh	P	5	5.205	0.003	9.027	0.002	20.019	0.002	95.75	935.8	0.5	5	25	1	0.013	removed from goniometer and re-positioned
RUSTUM3	A. Pradesh	P	5	5.212	0.002	9.036	0.003	20.019	0.002	95.82	937.9	0.4	4	27	1	0.014	
RUSTUM4	A. Pradesh	P	5	5.207	0.003	9.026	0.005	20.016	0.002	95.75	936.1	0.5	4	25	1	0.015	
RUSTUM5	A. Pradesh	P	5	5.203	0.004	9.023	0.005	20.023	0.002	95.79	935.2	0.7	8	30	2	0.021	goniometer speed 1'p min instead of 0.1
RUSTUM6	A. Pradesh	P	5	5.246	0.002	9.080	0.003	20.164	0.007	95.98	955.2	0.3	5	32	13	0.019	sample position too low, 0.5'p min
RUSTUM7	A. Pradesh	P	5	5.187	0.007	9.014	0.009	19.985	0.005	95.74	929.7	1.0	5	31	8	0.032	sample position too high, 0.5'p min
RUSTUM8	A. Pradesh	P	5	5.206	0.003	9.029	0.004	20.022	0.002	95.75	936.5	0.5	4	26	2	0.013	sample position normal, 0.1'p min
RUSTUM9	A. Pradesh	P	5	5.204	0.004	9.023	0.005	20.018	0.002	95.76	935.1	0.6	4	24	0	0.017	
RUSTUM10	A. Pradesh	P	5	5.204	0.003	9.028	0.004	20.015	0.002	95.77	935.5	0.4	4	24	0	0.011	
Average	N=10			5.206	0.003	9.031	0.004	20.029	0.003	95.79	937.0	0.53					
Std.dev.				0.015	0.001	0.017	0.002	0.0462	0.002	0.068	6.459	0.19					
Literature		Host = Host rock type															
B+S-1	Australia	P?	0	5.189		8.996		20.096									
B+S-2	A. Sponda	Sh	0	5.174		8.976		19.875									
B+S-4	A. Sponda	Sh	0	5.134		8.907		19.376									
B+S-5	California		0	5.211		9.038		19.947									
CHAT-Mu	synthet		0	5.188		8.990		20.152									
CHAT-Pg	synthet		0	5.130	0.001	8.893	0.002	19.270	0.003								
GUID-Mu	extrapol		0	5.183		8.994		20.123									
GUID-Ph	extrapol		0	5.291		9.169		19.960									
Y00-MuIM	synthet		0	5.208	0.010	8.995	0.020	10.275	0.005								
MOR-MuIM	Manitoba	P	0	5.230	0.020	9.000	0.020	10.072	0.005								
		Grp = Main rock groups															
		1-4 Alpine															
		5 Precambrian															
		6 Triassic															

\* Data from SCHWANDER, et al., 1968

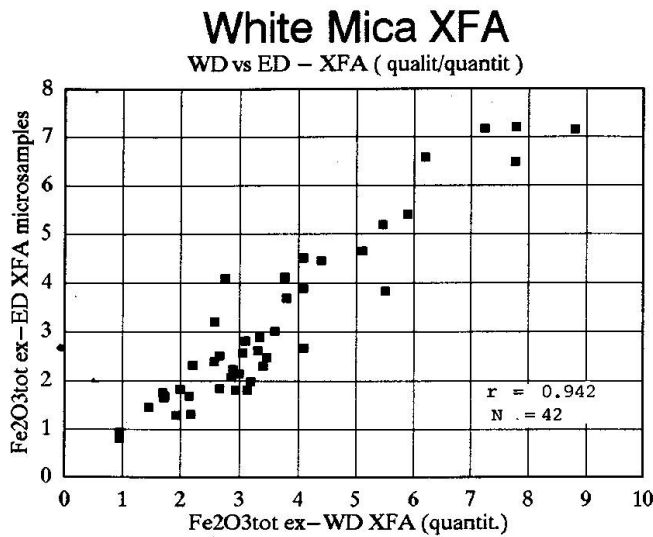


Fig. 3 Comparison of quantitative and qualitative X-ray fluorescence data ( $Fe_2O_3$  total).

Qualitative: 30 mg powdered mica on stretched foil (as for x-ray diffraction), ED-XFA  
 Quantitative: fusion with  $Li_2B_4O_7$  (Tab. 2), WD-XFA  
 The correlation coefficient ( $r=0.942, N=42$ ) is better than the one obtained by phengite analysis XRD versus XFA.

Some microsamples which were examined by XRD were analyzed qualitatively by ED-XFA (STERN, 1985) in order to examine the reliability of this fast and efficient method of non-destructive simultaneous instrumental analysis (Fig. 3).

The analyzed mica concentrates cover a wide, though not the complete compositional field of dioctahedral mica. They represent various types of host rock, like Alpine schists, gneisses, granites and pegmatites, Triassic granites, and Pre-cambrian pegmatites from Argentina, India, Sudan and Tanzania.

**Discussion**

Cell parameters of white mica display a large variation, much larger than the error of data determination (ref., see Fig. 4):

	phengite	muscovite	paragonite
a	5.291	5.183	5.135
b	9.169	8.990	8.993
c	19.947	20.152	19.270

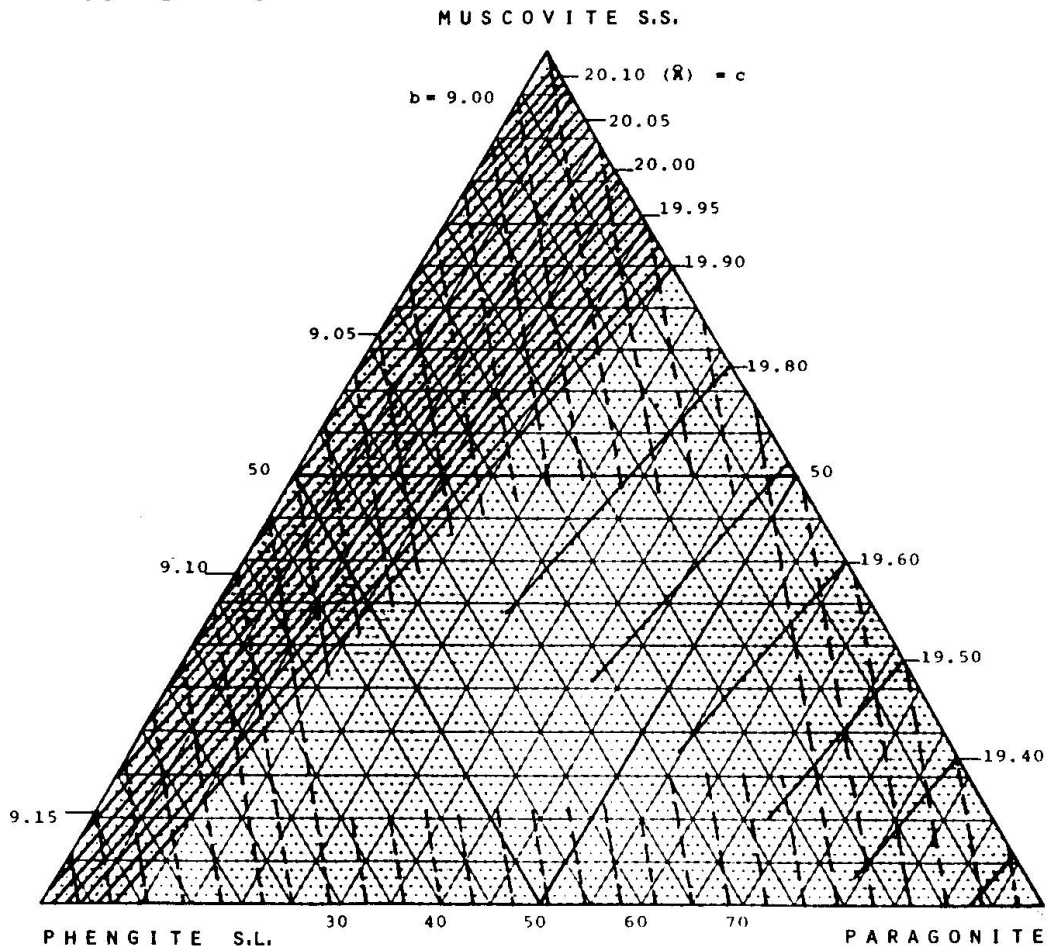


Fig. 4 Triangular plot of 2M1 dioctahedral micas muscovite – phengite – paragonite. Cell parameters b and c taken from literature: muscovite b, c after CHATTERJEE, JOHANNES, 1974; paragonite b, c after BORG and SMITH, 1969; phengite b after GUIDOTTI et al., 1989; phengite c after BORG and SMITH, 1969. The diagram enables – theoretically – the deduction of mica composition (% muscovite, paragonite, phengite) from experimentally determined cell parameters b and c. Far more reliable, and commonly used, is the direct chemical analysis.



The values for a and b have been correlated with the exchange of octahedral Al by Fe<sup>2+</sup> and Mg combined with exchange of tetrahedral Al<sup>3+</sup> by Si (Tschermak substitution, see e.g. GUIDOTTI et al., 1989). The value for c has been attributed to the exchange of interlayer K by Na (paragonite substitution, see e.g. CIPRIANI et al., 1968) – among other, less reported substitutions.


Corresponding correlation data published so far display a trendwise interdependence between diffraction and relevant chemical data, but the uncertainty of the correlation has been such that a quantitative use of b- or c-parameters for phengite or paragonite analysis seems hardly possible.

When b- and c-parameters of pure end members phengite, paragonite and muscovite (taken from literature) are combined in a triangular grid, it


is – theoretically – possible to determine e.g. the phengite or paragonite content of an unknown white mica (Fig. 4). If results of such a procedure, however, are controlled by chemical analyses, the agreement of diffractometric and chemical data is not too encouraging:

	phengite		paragonite		muscovite s.s.		
	XRD	XFA	XRD	XFA	XRD	XFA	(%)
Gli-04	8	14	7	1	85	85	
Gli-11	19	45	20	0	61	65	
KAW-083	21	24	6	0	73	75	
KAW-160	29	29	8	1	63	70	
KAW-165	42	52	6	1	52	47	
KAW-207	60	50	0	0	40	50	
Vz-477	35	21	0	2	65	77	
WS-72b	10	11	6	1	84	88	


White Mica 2M1 XRD vs XFA

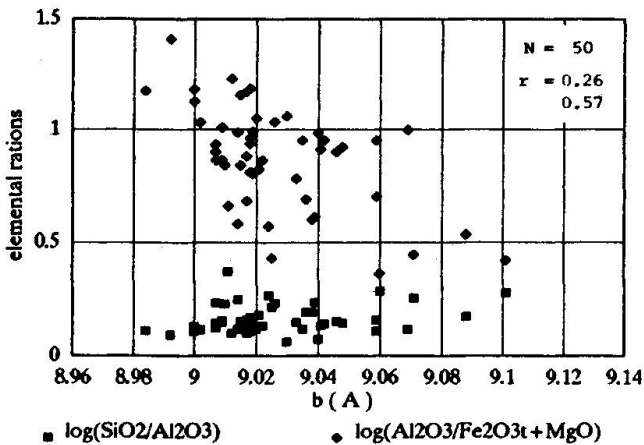

White Mica calculated "Phengite"

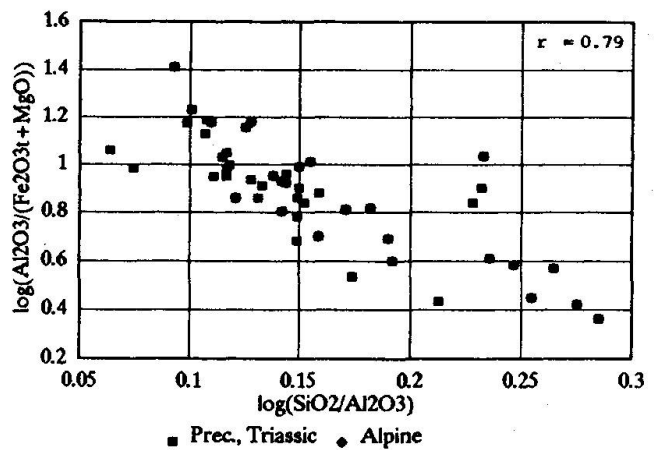

White Mica 2M1 XRD vs XFA

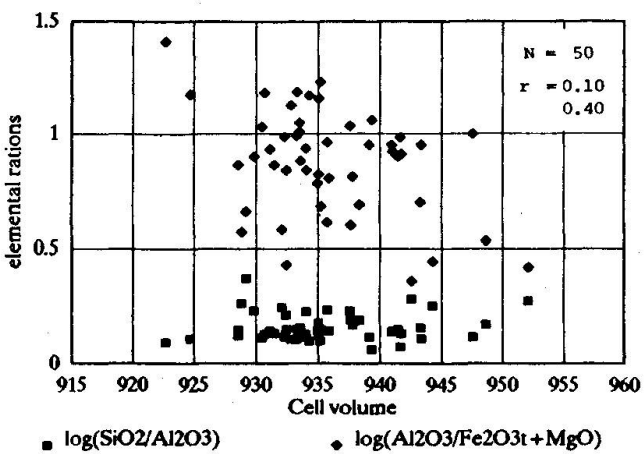

Alpine Mica 2M1 XRD vs XFA

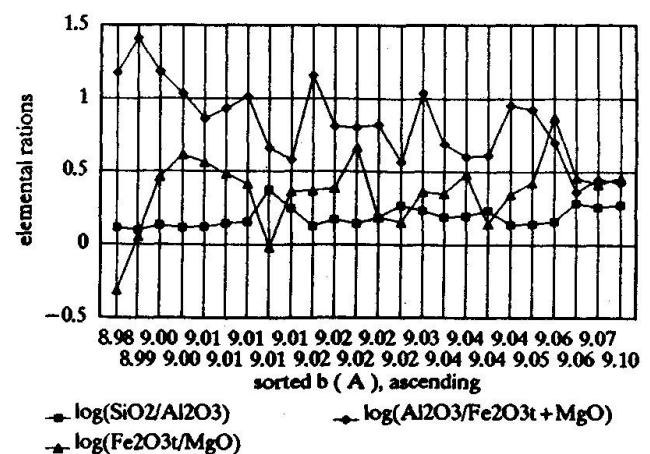


Fig. 5 Cell parameter b (XRD, experimental) and "phengite" content (XFA, experimental). Two elemental ratios are indicative, Si/Al connected with phengite content, and Al/Fe + Mg with ferrimuscovite and phengite content. Though a trendlike correlation between b and phengite content (XFA) exists, the interdependence is far too weak to be used for analytical purpose (i.e. phengite analysis by XRD).



The question arises (NÄEF, STERN, 1982), whether lacking accuracy of diffractometrical cell determination has been the reason for this poor correlation, or the complexity of chemical substitutions occurring.

The present powder diffraction data on disoriented microsamples display relatively small errors, being obviously not the reason for the large scatter around a regression curve e.g. a versus c or b versus volume; the slope of the regression line, again, corresponds well with the situation expected from literature (BORG and SMITH, 1969).

The correlation found between cell data and relevant chemical data (Fig. 5) resembles much from what is known from the literature and is too weak to be used as a calibration function. Since it can not be explained by errors of measurement, opposite effects of chemical substitutions have to account for it. Certain assumptions have been too simple:

- phengite consists of at least two different species, ferro- and picrophengite; the effect of  $\text{Fe}^{2+}$  and Mg on a and b parameters probably being different (Fig. 5);
- ferric iron is always present and may influence a and b by either replacing tetrahedral or octahedral Al;
- interlayer Na is scarce in phengitic mica and therefore hardly responsible for large deviations of a and b (Fig. 6);
- the size of c certainly depends on the Na-content of mica but on eventual Ca, Ba, Rb as

well, the latter often being neglected in chemical analysis, as is F whose influence on mica cell parameters is virtually unknown.

An intriguing fact is the obviously poor correlation of the c parameter with any of the chemical variables tested (Fig. 6). The use of basal spacings for paragonite quantification – as is common practice in petrographic literature – can therefore not be recommended. They are, however, helpful when paragonite has to be identified in presence of muscovite.

#### Acknowledgements

Mica samples have been provided by Dr. H.H. Klein, Schweiz. Isolawerke, Breitenbach; by Mr. Askury Abd. Kadir, Geol. Survey of Malaysia, which is gratefully acknowledged. For critical reading I have to thank Prof. Dr. M. Frey, Mineralogical Institute, Basel University, and Dr. H.H. Klein, and for laboratory support Mrs S. Wüthrich and Mr. R. Handschin, both of Geochemical Laboratorium Mpl Basel.

#### References

- APPLEMAN, D.E. and EVANS, H.T., Jr. (1973): Indexing and least-squares refinement of powder diffraction data. Report PB 216188, U.S. Dept. Commerce, National Techn. Inf. Service, 5285 Port Royal Rd., Springfield, VA 22151.
- BORG, I.Y. and SMITH, D.K. (1969): Calculated X-ray powder patterns for silicate minerals. Mem. 122, Boulder CO, Geol. Soc. Amer.
- CIPRIANI, C., SASSI, F.P. and VITERBO-BASSANI, C. (1968): La composizione delle miche chiare in rapporto con le costanti reticolari e col grado metamorfico. *Rend. Soc. Ital. Mineral. Petrol.*, 24, 153–187.
- CHATTERJEE, N.D. and JOHANNES, W. (1974): Thermal stability and standard thermodynamic properties of synthetic 2M1 muscovite  $\text{KAl}_2(\text{AlSi}_5\text{O}_{10})(\text{OH})_2$ . *Contrib. Mineral. Petrol.* 48, 89.
- CHATTERJEE, N.D. (1974): X-ray powder pattern and molar volume of synthetic 2M-paragonite: a refinement. *Contrib. Mineral. Petrol.* 43, 25.
- GUIDOTTI, C.V., SASSI, F.P. and BLENCOE, J.G. (1989): Compositional controls on the a and b cell dimensions of 2M1 muscovite. *Eur. J. Mineral.* 1, 71–84.
- HANDSCHIN, R. and STERN, W.B. (1990): Ein Präparationsverfahren zur röntgendiffraktometrischen und röntgenfluoreszenzspektrometrischen Analyse von Mikroproben. *Siemens Analysentechn. Mitt.* 319.
- NÄEF, U. and STERN, W.B. (1982): Some critical remarks on the analysis of phengite and paragonite components in muscovite by X-ray diffractometry. *Contrib. Mineral. Petrol.* 79, 35.
- SCHWANDER, H., HUNZIKER, J. and STERN, W. (1968): Zur Mineralchemie von Hellglimmern in den Tessiner Alpen. *Schweiz. Mineral. Petrogr. Mitt.* 48, 357.
- STERN, W.B. (1979): Probleme der quantitativen röntgenspektrometrischen Analyse von Hauptkomponenten und Spuren in geologischen Proben. *Schweiz. Mineral. Petrogr. Mitt.* 59, 83.

### White Mica 2M1 XRD vs XFA

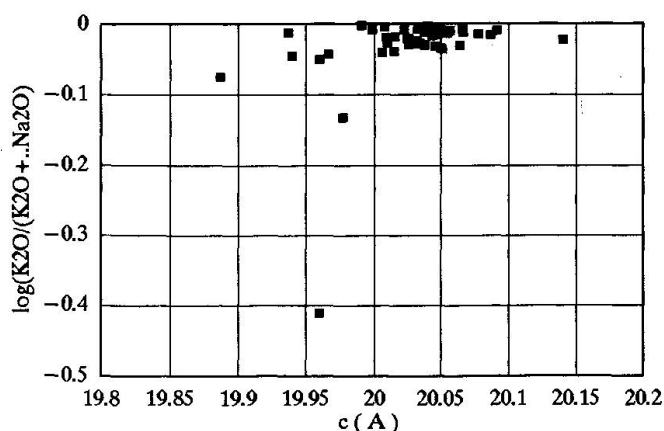


Fig. 6 Cell parameter c and paragonite content (XFA). Compositional variation of the paragonite content is 0 to 25%, main part of points plotting between 0 and 10% paragonite. No correlation between paragonite percentage and cell parameter c is statistically ascertained (Alpine muscovites s.l. N = 23,  $r = 0.50$ ; Precambrian, Triassic muscovites s.l. N = 19,  $r = 0.15$ ).

STERN, W.B. (1985): Zur Simultananalyse von Silicaten (Hauptkomponenten, Spuren) mittels energiedispersiver Röntgenfluoreszenz-Spektrometrie (EDS-XFA). *Fresenius Z. Anal. Chem.* 320, 6–14.

STERN, W.B. (1987): Determination of mica cell parameters by X-ray powder diffractometry – a case study. *Powder Diffraction*, 2, 249.

Manuscript received August 15, 1990; revised manuscript accepted December 11, 1990.

### Appendix: Instrumental conditions

#### A. X-ray diffraction (XRD)

apparatus D-500, Siemens GFR  
 excitation Cu 40 kV, 30 mA, no primary filter, secondary graphite monochromator  
 apertures automatic divergence slit set at 3, 3–3 entrance aperture, 1–0.05–0.15 secondary side  
 exposure 0.1  $2\theta$  P min., angular increment 0.02  $2\theta$  angular limits 3–73  $2\theta$   
 software DIFFRAC-500  
 least squares refinement after APPLEMAN, EVANS, 1973, 3 basal reflections pre-indexed, minimum error for rejection 0.05 2 $\theta$ ; only reflections > 10 cps were taken for refinement, low scaling factor of 0.1 for reflections below 20  $2\theta$   
 specimen 30 mg powdered mica on Makrofol (KG, Bayer) foil 40 mm  $\phi$  electrostatically disoriented (HANDSCHIN, STERN, 1990)

#### B. X-ray fluorescence (XFA); wavelength-dispersive (WD-XFA)

apparatus SRS-303, Siemens GFR  
 excitation Rh-end window tube, variable according to chemical element; 40 to 60 kV, 70 to 40 mA, 10 to 100 sec  
 analyzers In Sb for Si, P, S, Cl  
 multilayer OVO-55 for Al, Mg, Na, F  
 LiF for K- and L-lines of heavy elements  
 fitted background correction for traces  
 software SPECTRA/AT (Siemens)  
 routines QUANTXV, QUANTIX  
 data management with LOTUS 1–2–3  
 specimen main constituents: fused glass beads consisting of 150 mg ignited sample powder + 2350 mg  $\text{Li}_2\text{B}_4\text{O}_7$  annealing in 95 Pt–5 Au crucible, diameter 32 mm, inductive furnace (STERN, 1979);  
 trace elements: 800 mg dried sample powder pressed into Al-rings, diameter 20 mm, elvacite binder

#### energy-dispersive (ED-XFA)

apparatus Spectrace-5000, Tracor X-ray, U.S.A.  
 excitation W-tube (127 microns Be window), 6 to 50 kV, 0.35 to 0.20 mA, integration time per procedure 200 sec, dead time kept below 40%  
 analyzer solid state detector (Li)–Si, with ultrathin Be-window, 7.6 microns  
 software Tracor X-ray, running on IBM AT 80-311 314 Mb, 2 Mb RAM  
 specimen 30 mg on stretched Makrofol foil, as described under section XRD